

Deflection-time Behavior and Fire Resistance of GFRP-steel Reinforced Concrete Beams Exposed to Different Fire Conditions



Det Van Doan^{1,2} and Vui Van Cao^{1,2,*} 

¹Faculty of Civil Engineering, Ho Chi Minh City University of Technology (HCMUT), 268 Ly Thuong Kiet Street, Dien Hong Ward, Ho Chi Minh City, Vietnam

²Vietnam National University, Ho Chi Minh City (VNU-HCM), Linh Xuan Ward, Ho Chi Minh City, Vietnam

Abstract:

Introduction/Objective: This paper explores the effects of fire conditions and reinforcement configurations on the deflection-time behavior and fire resistance of hybrid glass fiber-reinforced polymer (GFRP)-steel-reinforced concrete (RC) beams. The reinforcement configurations of these hybrid beams are characterized by ρ_{ffs} , which is the ratio of GFRP area to the total area of both GFRP and steel. The considered values of ρ_{ffs} were 0 (steel RC beams), 0.2, 0.4, 0.6, 0.8, and 1.0 (GFRP RC beams).

Methods: SAFIR finite element models were developed, verified, and used for analyses. The fire resistance and deflection-time behavior of hybrid beams were determined.

Results: When ρ_{ffs} increased from 0 to 1, the fire resistance of hybrid beams was shifted from the state governed by the deflection limit to the state governed by the deflection rate limit. Increasing the number of fire-exposed surfaces from 1 to 4 detrimentally affected the deflection-time behavior of the beams. Compared with exposure to the bottom surface, exposure to 2, 3, and 4 surfaces significantly decreased the fire resistance by up to 74.2%. The increases in ρ_{ffs} and the number of fire-exposed surfaces detrimentally affected the deflection-time behavior and fire resistance of hybrid beams.

Discussion: This phenomenon is attributed to the faster reduction in the mechanical properties of GFRP compared with those of steel. In addition, the cross-sectional temperatures were significantly affected by the number of fire-exposed surfaces.

Conclusion: Both ρ_{ffs} and the number of fire-exposed surfaces should be considered in the assessment of hybrid GFRP-steel RC beams exposed to fire.

Keywords: GFRP, GFRP-steel reinforcement, Reinforced concrete beam, Fire, Fire resistance, Deflection-time behavior.

© 2026 The Author(s). Published by Bentham Open.

This is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International Public License (CC-BY 4.0), a copy of which is available at: <https://creativecommons.org/licenses/by/4.0/legalcode>. This license permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

*Address correspondence to this author at the Faculty of Civil Engineering, Ho Chi Minh City University of Technology (HCMUT), 268 Ly Thuong Kiet Street, Dien Hong Ward, Ho Chi Minh City, Vietnam and Vietnam National University Ho Chi Minh City (VNU-HCM), Linh Xuan Ward, Ho Chi Minh City, Vietnam; E-mail: cvvui@hcmut.edu.vn

Cite as: Van Doan D, Van Cao V. Deflection-time Behavior and Fire Resistance of GFRP-steel Reinforced Concrete Beams Exposed to Different Fire Conditions. Open Civ Eng J, 2026; 20: e187414955012. <http://dx.doi.org/10.2174/01187414955012260828061310>



Received: April 28, 2026
Revised: June 09, 2026
Accepted: July 21, 2026
Published: August 31, 2026



Send Orders for Reprints to
reprints@benthamscience.net

1. INTRODUCTION

Corrosion is an issue for steel-reinforced concrete (RC) structures [1]. In contrast, fiber-reinforced polymer (FRP)

has high corrosion resistance, high tensile strength, and low weight. FRP has been used to reinforce [2] and repair/strengthen [3] concrete structures. However, FRP works elastically up to its ultimate, resulting in brittle

failure. Therefore, the combination of FRP and steel (hybrid FRP-steel) for the reinforcement of concrete structures leverages the advantages of both materials while mitigating the corrosion issues of steel.

The performance of hybrid FRP-steel RC beams at room temperature has been studied by the research community. The strength and ductility of concrete beams over-reinforced with hybrid GFRP-steel were greater than those reinforced just with GFRP [4]. Increasing the equivalent reinforcement ratio negatively affected the ductility of hybrid FRP-steel RC beams [5]. The FRP-to-steel area ratios significantly influenced the strength and ductility of hybrid beams [6]. Good ductility and high strength of hybrid GFRP-steel RC beams were confirmed by Qu *et al.* [7]. Increasing the steel ratio improved the stiffness and ductility of hybrid FRP-steel RC beams [8]. Increasing the steel ratio enhanced the serviceability and ductility of GFRP-steel RC beams [9]. Kadhim and Zinkaah [10] developed a formula for predicting the load-carrying capacity of hybrid RC beams. Alsuhaibani and Aldukail [11] confirmed that hybrid GFRP-steel reinforcement improved the strength, stiffness, and ductility of RC beams when sufficient stirrups were used. Investigations have also been conducted on hybrid beams made of geopolymers concrete [12] and concrete beams with GFRP-steel hybrid stirrups [13].

When a fire occurs in a building, the fire directly heats the beams from the bottom, where the tension reinforcement is located. The reduction in the mechanical properties of tension reinforcement significantly reduces the load-carrying capacity of the beams. The divisions in a building can result in different fire conditions for the beams. For example, a wall partition can be constructed within the frame structure, functioning as the frame infill, and it can create a fire condition on one side of the beam. Generally, beams can be exposed to fire on one, two, three, or four surfaces. Evaluating the load-carrying capacity of beams exposed to different fire conditions may thus be necessary to account for practical considerations.

However, the performance of hybrid FRP-steel RC beams exposed to fire appears to have been only limitedly explored. Masood and Nadjai [14] found that hybrid CFRP-steel RC beams exhibited higher stiffness and better ductility than FRP- or steel-only RC beams. Fire resistance of hybrid GFRP-steel RC beams was affected by the arrangement of CFRP bars and steel bars [15]. When tensile steel and GFRP bars were arranged in the outer and inner layers, respectively, the ultimate strength of hybrid GFRP-steel RC beams was 35% higher than that with a one-layer arrangement [16]. Exposure to 700°C reduced both ductility and strength of hybrid GFRP-steel RC beams by 53% and 12%, respectively [17]. Hybrid BFRP-steel reinforcement improved the shear strength and crack stiffness of concrete beams exposed to 500°C for 2 hours [18]. Exposure to constant 300°C and 600°C for 60 minutes reduced the stiffness of GFRP-steel RC beams by 17% and 31%, respectively, compared with that of beams reinforced with steel bars covered with GFRP (hybrid bars) [19].

Different characteristics of hybrid GFRP-steel RC beams exposed to fire have been investigated, as reviewed above. However, investigations on the effects of different fire conditions and ρ_{ffs} on the deflection-time behavior and fire resistance are scarce in the literature and are thus the aim of this study. Toward these aims, finite element models of hybrid GFRP-steel RC beams with ρ_{ffs} varying from 0 to 1 were developed in SAFIR software. The models were verified by comparing them with available test results, which showed good agreement. The verified models were used for modeling hybrid GFRP-steel RC beams exposed to different fire conditions. The obtained results were analyzed to conclude the effects of fire conditions and ρ_{ffs} on the fire performance and resistance of GFRP-steel RC beams.

2. MATERIALS AND METHODS

2.1. SAFIR Modeling

SAFIR models structures exposed to fire in two stages, namely thermal analysis and mechanical analysis. Thermal analysis results in the distributions of temperature in cross-sections, which are then used for mechanical analysis.

In thermal modeling, the STEELEC2EN model was adopted for reinforcement (steel and GFRP). CONCEC 2020 model in Eurocode 2 [20] was used to model concrete. In structural modeling, a normal concrete (NS CONCRETE) model was used. The reduction (k_c) in compressive strength of concrete adopted in Eurocode 2 [20] was used. It is expressed by Equation 1, where T is the temperature. The reduction (k_{ec}) in elastic modulus of concrete at high temperature recommended by Gernay and Franssen [21] is expressed by Equation 2. The reductions in yield strength and elastic modulus of steel at elevated temperatures recommended by Eurocode 2 [20] are expressed by Equations 3 and 4, respectively. The reductions in tensile strength (k_f) and elastic modulus (k_{ef}) of GFRP bars are expressed by Equations 5 and 6 [22], respectively.

$$\begin{aligned} k_c &= 1 \quad \text{if } T \leq 100^\circ\text{C} \\ k_c &= 1.067 - 0.00067T \quad \text{if } 100^\circ\text{C} \leq T \leq 400^\circ\text{C} \\ k_c &= 1.44 - 0.16T \quad \text{if } 400^\circ\text{C} \leq T \leq 900^\circ\text{C} \\ k_c &= 0 \quad \text{if } 900^\circ\text{C} \leq T \end{aligned} \quad (1)$$

$$\begin{aligned} k_{ec} &= 1.0233 - 0.0018T \quad \text{if } T \leq 300^\circ\text{C} \\ k_{ec} &= 0.8038 - 0.001T \quad \text{if } 300^\circ\text{C} \leq T \leq 600^\circ\text{C} \\ k_{ec} &= 0.2517 - 9 \times 10^{-5}T \quad \text{if } 800^\circ\text{C} \leq T \end{aligned} \quad (2)$$

$$\begin{aligned} k_s &= 1 \quad \text{if } T \leq 350^\circ\text{C} \\ k_s &= 1.889 - 0.00257T \quad \text{if } 350^\circ\text{C} \leq T \leq 700^\circ\text{C} \\ k_s &= 0.24 - 0.002T \quad \text{if } 700^\circ\text{C} \leq T \leq 1200^\circ\text{C} \\ k_s &= 0 \quad \text{if } 1200^\circ\text{C} \leq T \end{aligned} \quad (3)$$

$$\begin{aligned}
k_{Es} &= 1 \quad \text{if } 0 \leq T \leq 100^\circ\text{C} \\
k_{Es} &= 1.1 - 0.001T \quad \text{if } 100^\circ\text{C} \leq T \leq 500^\circ\text{C} \\
k_{Es} &= 2.05 - 0.0029T \quad \text{if } 500^\circ\text{C} \leq T \leq 600^\circ\text{C} \\
k_{Es} &= 1.39 - 0.0018T \quad \text{if } 600^\circ\text{C} \leq T \leq 700^\circ\text{C} \\
k_{Es} &= 0.41 - 0.0004T \quad \text{if } 700^\circ\text{C} \leq T \leq 800^\circ\text{C} \\
k_{Es} &= 0.27 - 0.000225T \quad \text{if } 800^\circ\text{C} \leq T \leq 1200^\circ\text{C} \\
k_{Es} &= 0 \quad \text{if } 1200^\circ\text{C} \leq T
\end{aligned} \tag{4}$$

$$\begin{aligned}
k_f &= 1 - 0.0025T \quad \text{if } 0 \leq T \leq 400^\circ\text{C} \\
k_f &= 0 \quad \text{if } 400^\circ\text{C} \leq T
\end{aligned} \tag{5}$$

$$\begin{aligned}
k_{Ef} &= 1 \quad \text{if } 0 \leq T \leq 100^\circ\text{C} \\
k_{Ef} &= 1.25 - 0.0025T \quad \text{if } 100^\circ\text{C} \leq T \leq 300^\circ\text{C} \\
k_{Ef} &= 2 - 0.005T \quad \text{if } 300^\circ\text{C} \leq T \leq 400^\circ\text{C} \\
k_{Ef} &= 0 \quad \text{if } 400^\circ\text{C} \leq T
\end{aligned} \tag{6}$$

2.2. Verifications

The available test results for RC beams exposed to fire were selected for verification. The RC beam in fire experimentally tested by Song *et al.* [23] was selected. Figure 1 shows the configuration and details of the beam. The compressive strength of concrete was 25.8 MPa. Steel bars $\phi 16$ and $\phi 25$ had yield strengths of 445 MPa and 451 MPa, respectively. The concrete cover thickness was 25 mm. The elastic moduli of steel and concrete were 2×10^5 MPa and 2.4×10^4 MPa, respectively. The Poisson ratio was 0.3.

Convection coefficient hot and convection coefficient cold were 25 and 4, respectively. Relative emissivity was 0.7. Thermal conductivity was 0.5. Moisture content was 1.43%. These are default values in SAFIR. The beam was exposed to fire on the bottom and two side surfaces, and the furnace temperature-time curve [23] is presented in Fig. (2). This fire was assigned for the bottom and two side surfaces, while the top surface was assigned by F20 because it was not exposed to fire. Figure 3a shows these assigned fire conditions. The cross-sections were meshed as shown in Fig. (3b). Fig. (4a and b) show examples of temperature distributions at 60 and 120 minutes, respectively. The fire duration significantly increased the temperature in the cross-section.

The deflection-time curves obtained from SAFIR and the experimental result [23] are compared in Fig. (5). The fire resistance obtained from the model was 185 minutes, which is close to the fire resistance of 192 minutes obtained from the experiment. The difference is only 3.65%, showing good agreement.

A similar modeling procedure was conducted for the GFRP RC beam tested by Yu and Kodur [24]. The cross-section of the beam was 305 mm in width and 533 mm in height. The span length was 6010 mm. The tested beam was reinforced with 8 (19 GFRP bars), as shown in Fig. (6a). The convection coefficients for hot and cold are 25 and 4, respectively. The deflection-time curve obtained from the SAFIR model is plotted in Fig. (6b), compared with that from the experiment. The fire resistances obtained from the SAFIR modeling and the experiment were 67 minutes and 64 minutes, respectively. Thus, the difference is only 4.7%, indicating satisfactory model accuracy.

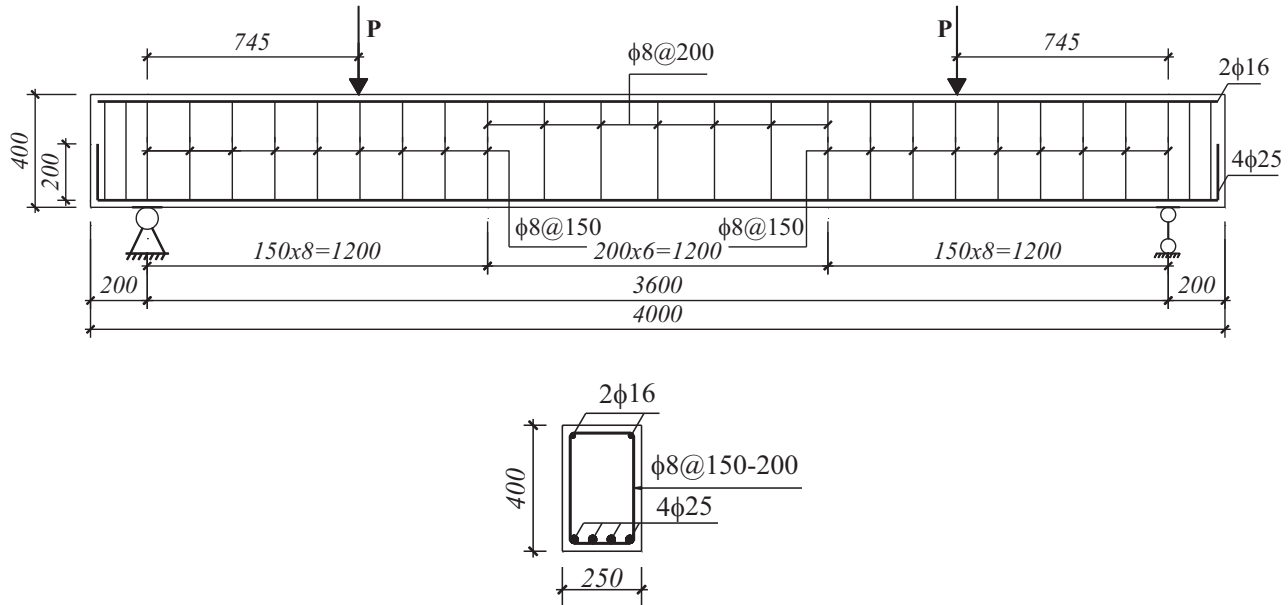


Fig. (1). Beam B2 tested by Song *et al.* (unit: mm). Reproduced from Y. Song, C. Fu, S. Liang, A. Yin, and L. Dang. Fire resistance investigation of simple supported RC beams with varying reinforcement configurations", *Adv. Civ. Eng.*, vol. 2019, no. 1, p. 8625360, under the permission of the Creative Commons Attribution Non-Commercial License 4.0 (CC BY-NC 4.0). [23].

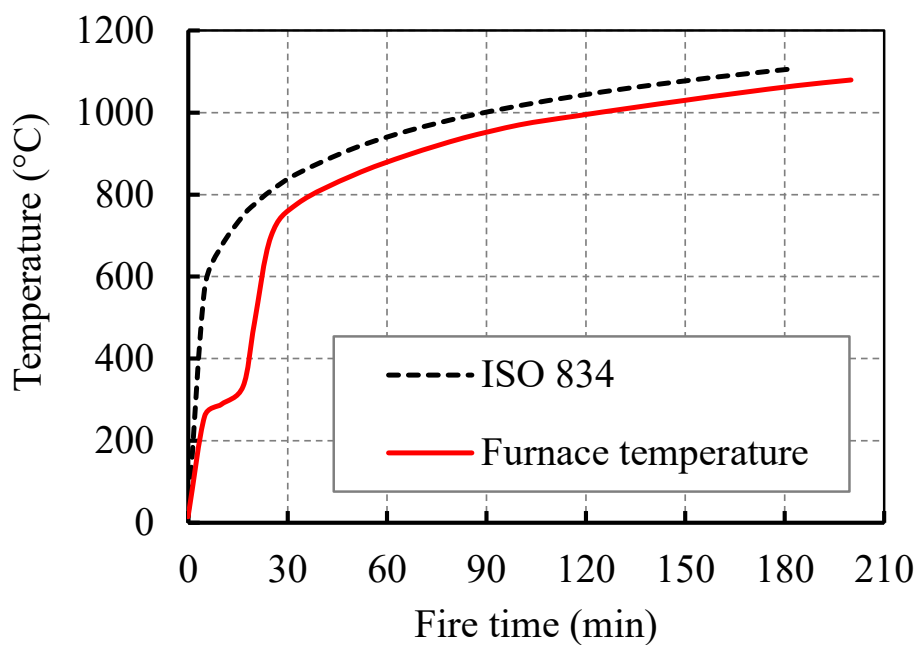


Fig. (2). Furnace temperature-time curve and ISO 834 fire curve. Reproduced from Y. Song, C. Fu, S. Liang, A. Yin, and L. Dang. Fire resistance investigation of simple supported RC beams with varying reinforcement configurations", *Adv. Civ. Eng.*, vol. 2019, no. 1, p. 8625360, under the permission of the Creative Commons Attribution Non-Commercial License 4.0 (CC BY-NC 4.0). [23].

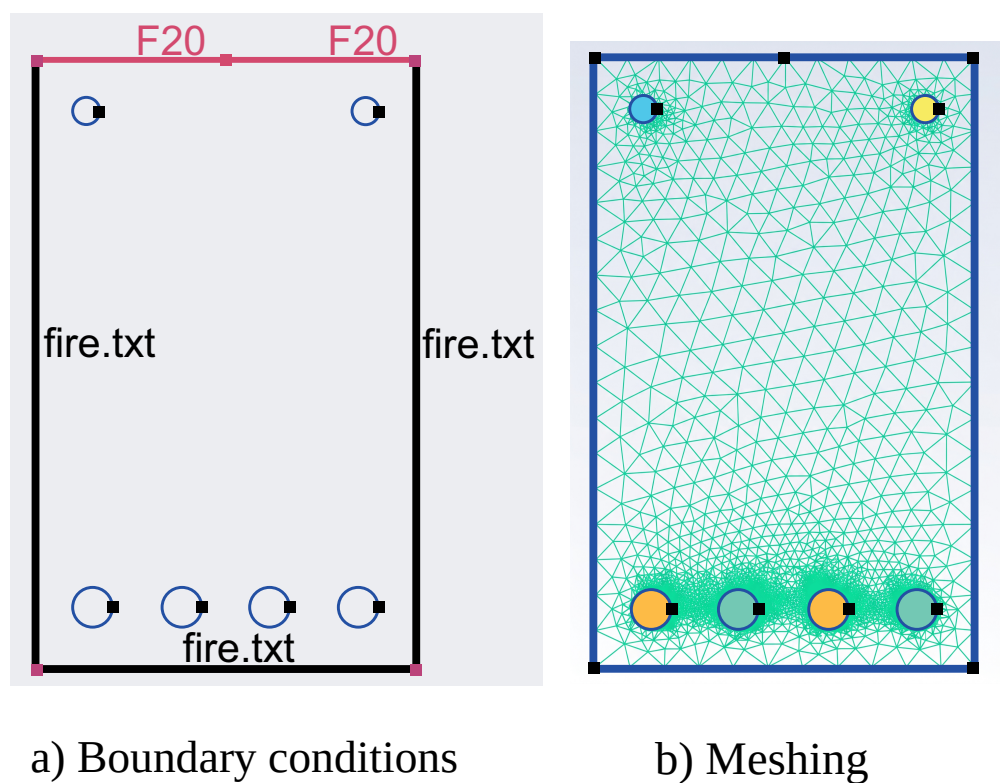


Fig. (3a, b). 2D model for thermal modeling.

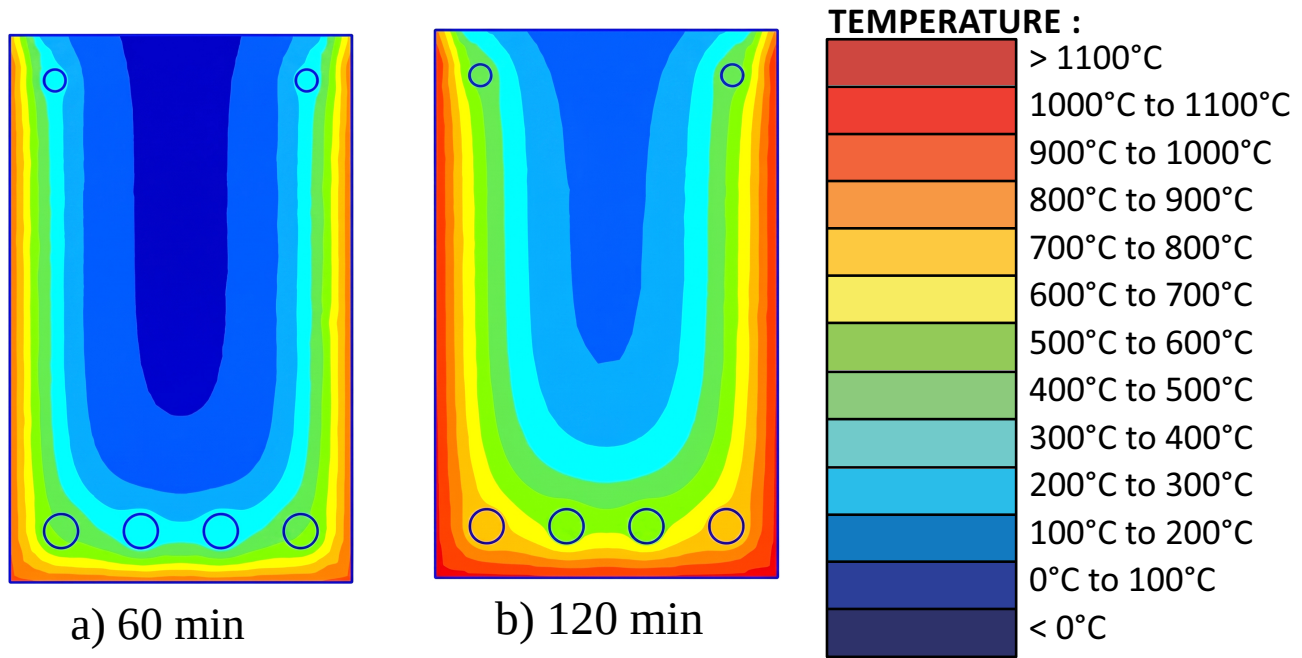


Fig. (4a, b). Temperature distributions in cross-sections at different fire times.

2.3. Hybrid GFRP-steel RC Beams for Analyses

Steel RC beams: The beam B2 tested by Song *et al.* [23] was modified for analyses. The analyzed beams had a cross-section of $b \times h = 250 \times 400$ mm and a span length of 3.6 m. Concrete had an equivalent compressive strength

of 25.8 MPa. The longitudinal compression reinforcement was $2\phi 12$ with a yield strength of 445 MPa. The longitudinal tension reinforcement was $5\phi 16$ with a yield strength of 451 MPa and an elastic modulus of 200 GPa. Stirrups were steel $\phi 8$ with a spacing of 200 mm.

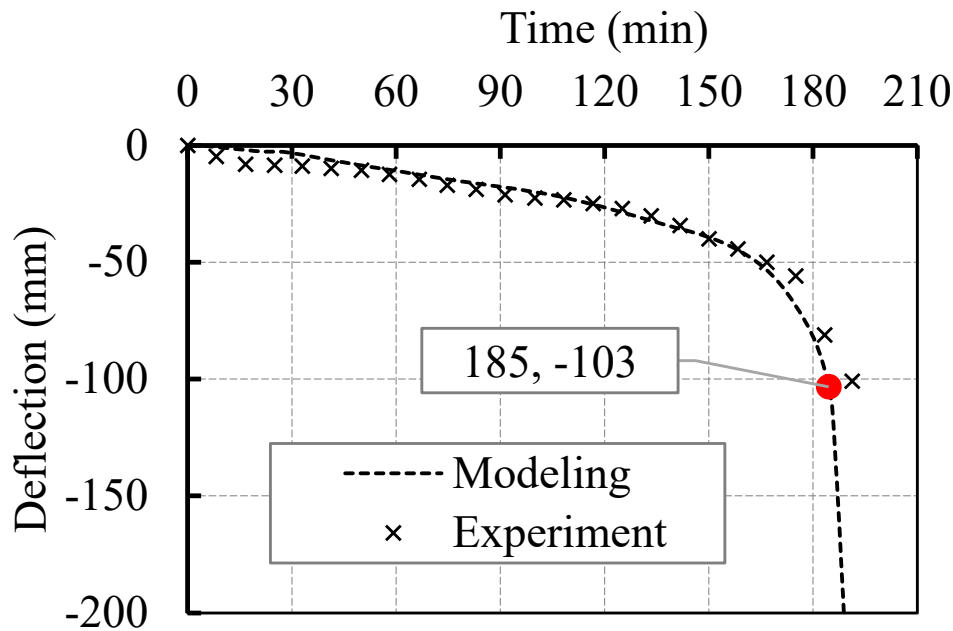


Fig. (5). SAFIR and Song *et al.* deflection-time curves. Reproduced from Y. Song, C. Fu, S. Liang, A. Yin, and L. Dang. Fire resistance investigation of simple supported RC beams with varying reinforcement configurations", Adv. Civ. Eng., vol. 2019, no. 1, p. 8625360, under the permission of the Creative Commons Attribution Non-Commercial License 4.0 (CC BY-NC 4.0). [23].

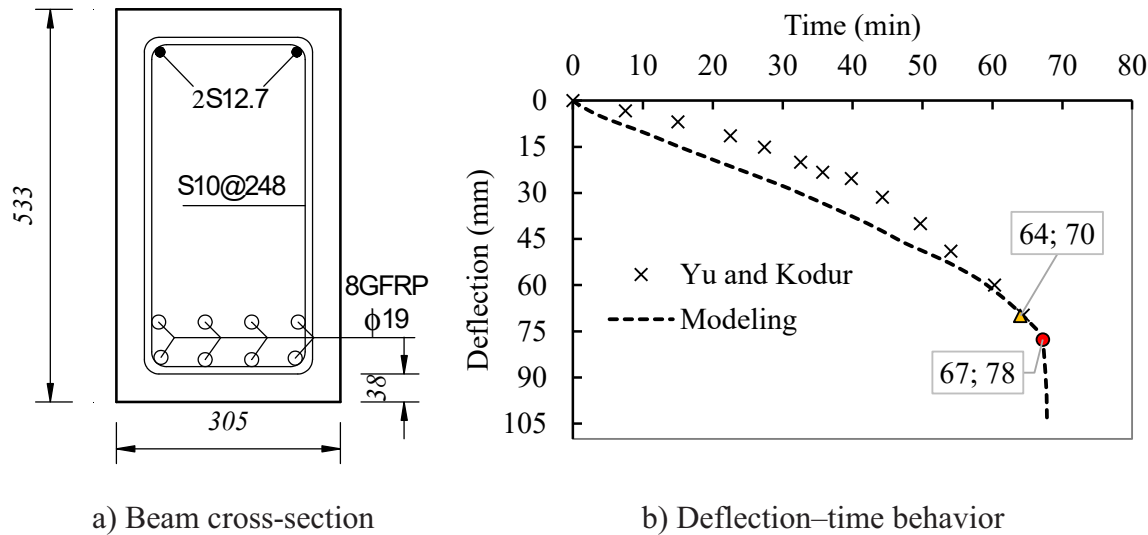


Fig. (6a, b). GFRP RC beam tested by Yu and Kodur and comparison of deflection-time curves [24].

Hybrid GFRP-steel RC beams: $\phi 16$ GFRP bars were used to replace steel bars in the above steel RC beams. One, two, three, and four GFRP bars were used to replace one, two, three, and four steel bars in the tensile steel reinforcement, respectively, to produce four hybrid GFRP-steel RC beams.

GFRP RC beam: Five steel bars in the tension zone of

the steel RC beam were replaced by five GFRP bars.

Table 1 summarizes the configurations of these beams. The value of $\rho_{f/fs}$ varies from 0 to 1 with an interval of 0.2. Figure 7 shows the cross-sections of these beams. GFRP bars had a tensile strength of 800 MPa, an elastic modulus of 45 GPa, and a Poisson coefficient of 0.2. The convection coefficients for hot and cold are 25 and 4, respectively.

Table 1. GFRP and steel reinforcement.

Combination	Reinforcement	GFRP Area A_f	Steel Area A_s	Total Reinforcement Area $A = A_f + A_s$	Ratio $\rho_{f/fs} = A_f / A$
		(mm ²)	(mm ²)	(mm ²)	
1	5S16	0.0	1005.3	1005.3	0.0
2	4S16+1G16	201.1	804.2	1005.3	0.2
3	3S16+2G16	402.1	603.2	1005.3	0.4
4	2S16+3G16	603.2	402.1	1005.3	0.6
5	1S16+4G16	804.2	201.1	1005.3	0.8
6	5G16	1005.3	0.0	1005.3	1.0

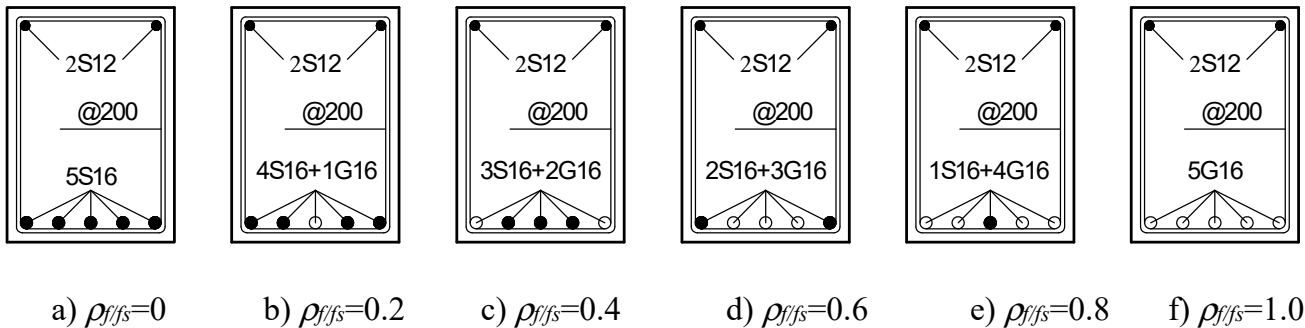


Fig. (7a-f). Hybrid GFRP-steel RC cross-sections of beams.

These hybrid GFRP-steel RC beams are exposed to fire from one surface (the bottom surface), two surfaces (the bottom and a side surface), three surfaces (the bottom and two side surfaces), and four surfaces. The applied fire was conforming to the ISO-834 standard fire, namely, FISO. The ambient temperature (F20) was assigned to the surface that was not exposed to fire. Figure 8 shows beams exposed to different fire conditions. Figure 9 shows an example of meshing, in which fine meshes were applied for reinforcement and adjacent regions to improve the accuracy of the models.

3. RESULTS AND DISCUSSION

3.1. Temperature Distribution in Hybrid GFRP-steel Cross-sections

Distributions of temperature in the cross-sections

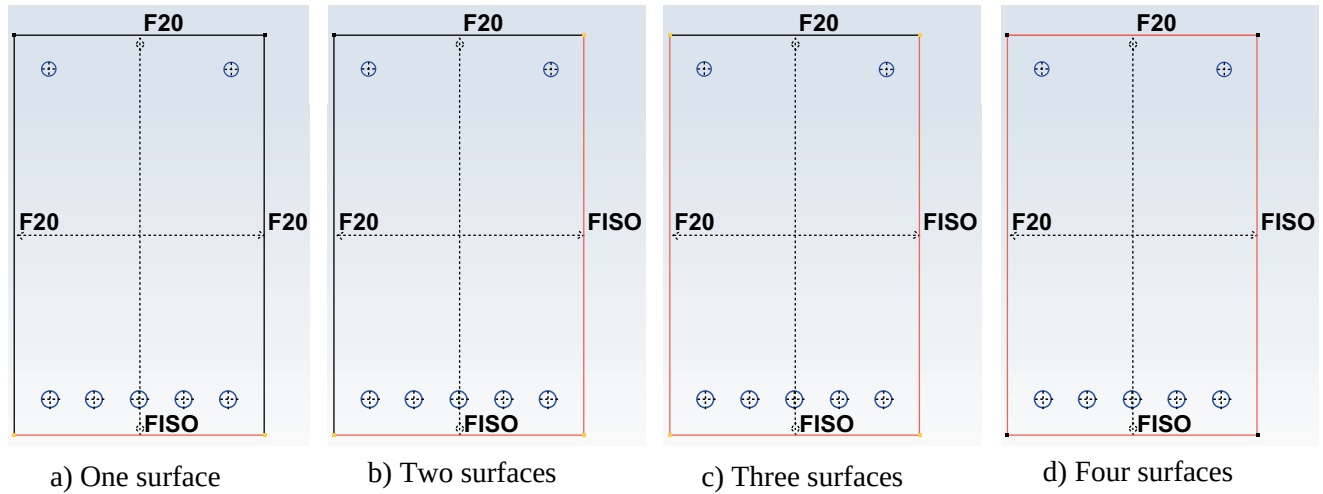


Fig. (8a-d). Beams exposed to different fire conditions.

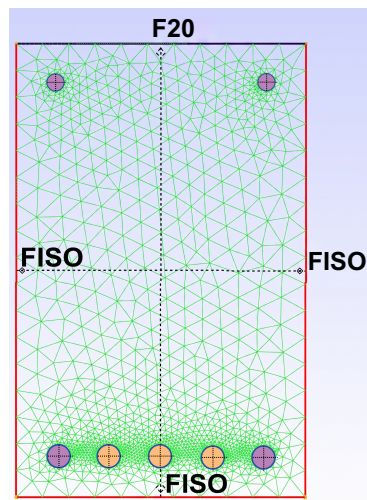


Fig. (9). Meshing of the cross-section.

exposed to fire from the bottom surface are presented in Fig. (10a-g). The temperature at the bottom surface is the highest, while the temperature from the mid-height to the top surface is unchanged, although the fire duration is up to 420 minutes Fig. (10g). This is the explanation for the long fire duration when the beams were exposed to fire from only the bottom surface. When exposed to fire from two surfaces, the temperature in the cross-sections (Fig. 11a-g) is significantly higher. The highest temperature is at the corner of the two fire-exposed surfaces.

Exposed to fire from three surfaces (Fig. 12a-d) and four surfaces (Fig. 13a-d), the temperature in the cross-sections is significantly increased. The fire durations required to reach extremely high temperatures are also significantly shorter than those for cross-sections exposed to fire from one or two surfaces.

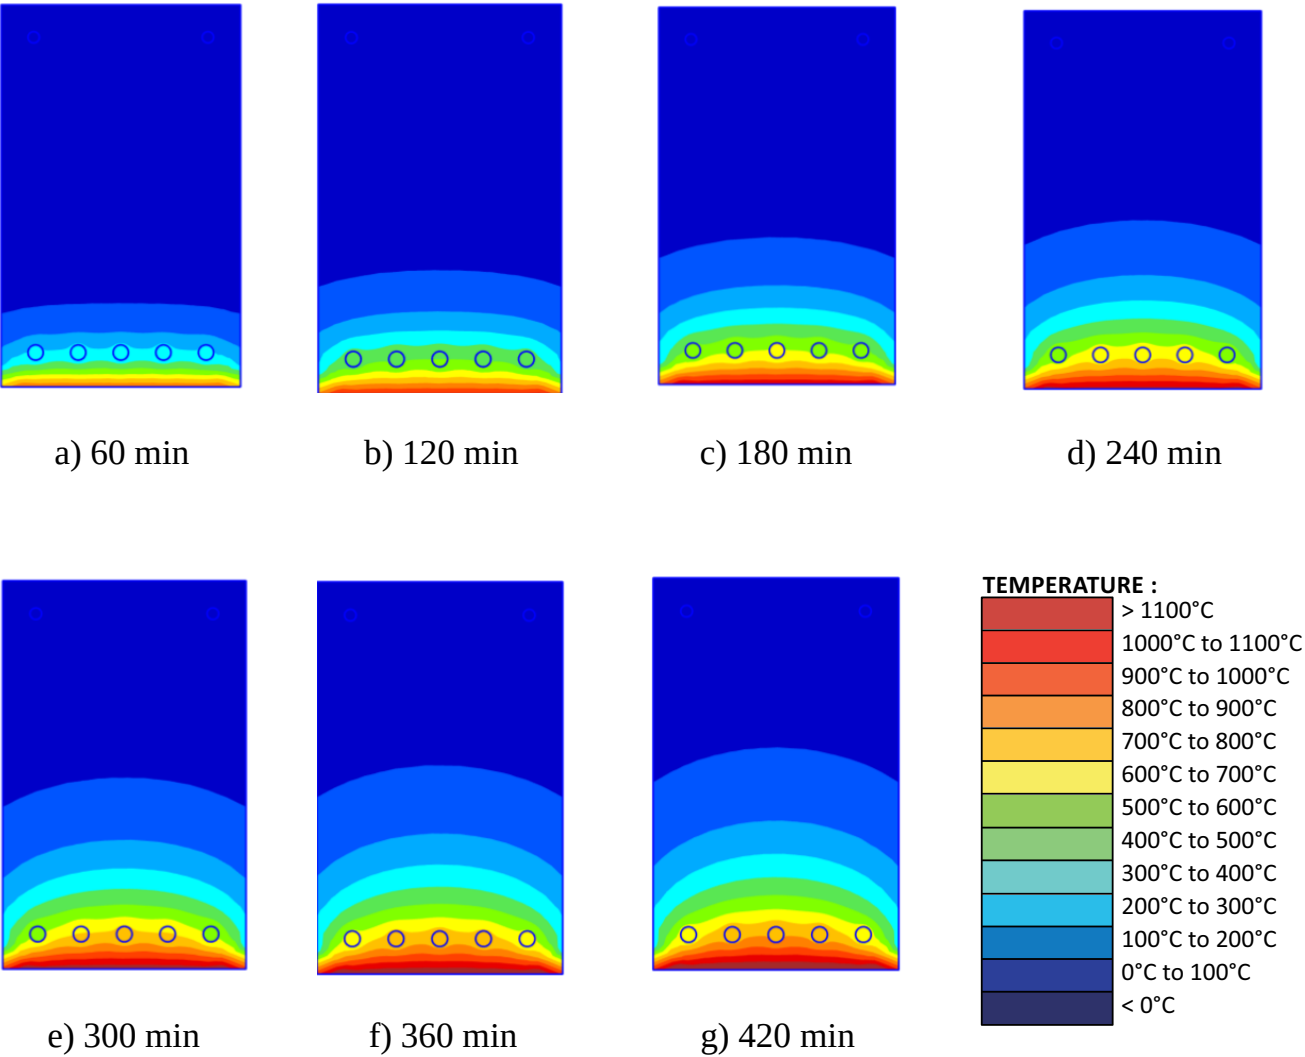


Fig. (10a-g). Distributions of temperature in cross-sections exposed to fire from the bottom surface.

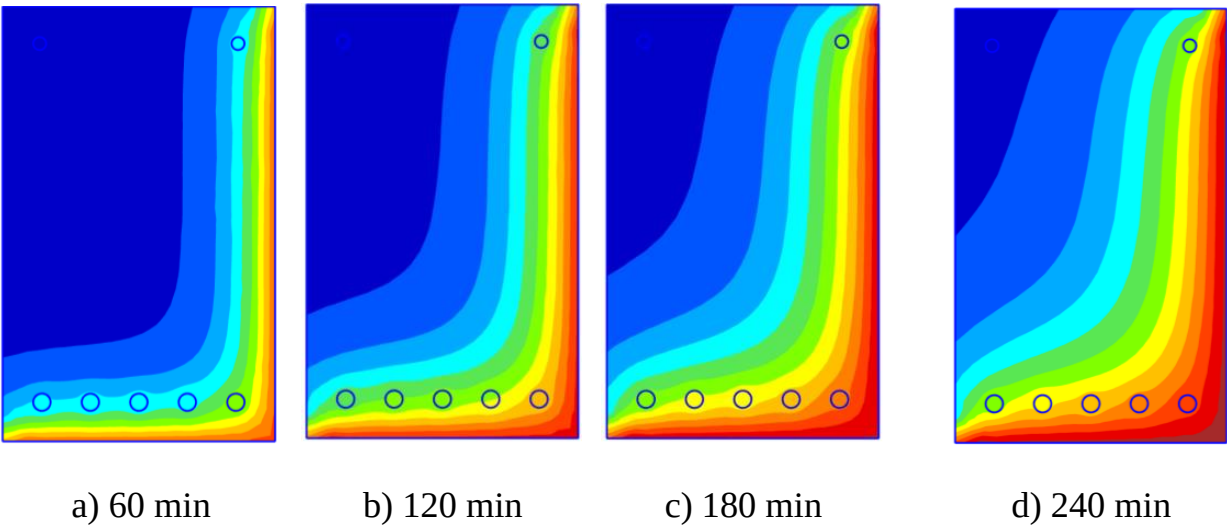


Fig. 11 contd.....

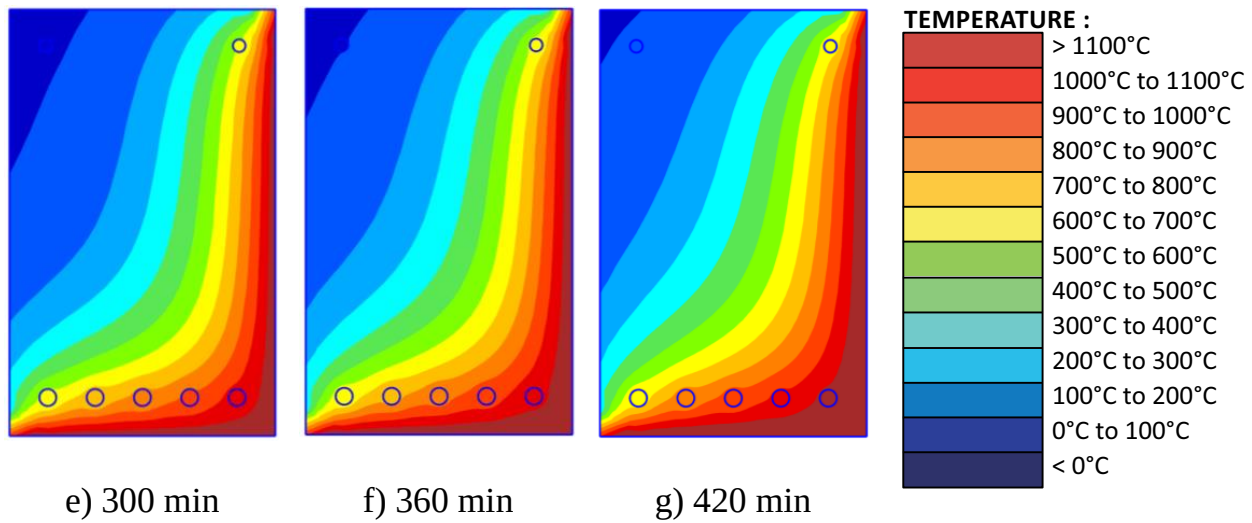


Fig. (11a-g). Distributions of temperature in cross-sections exposed to fire from two surfaces.

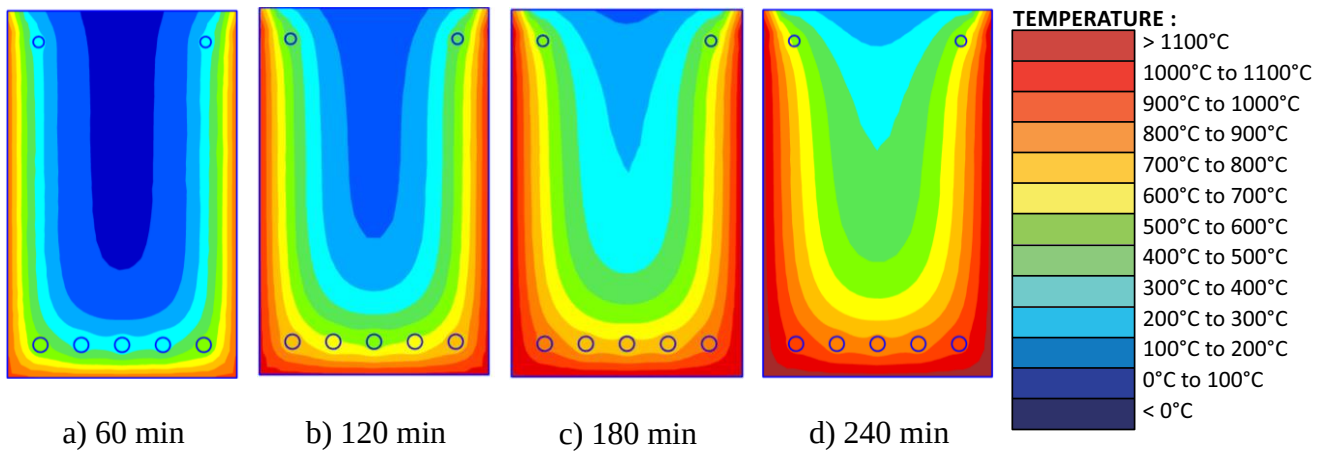


Fig. (12a-d). Distributions of temperature in cross-sections exposed to fire from three surfaces.

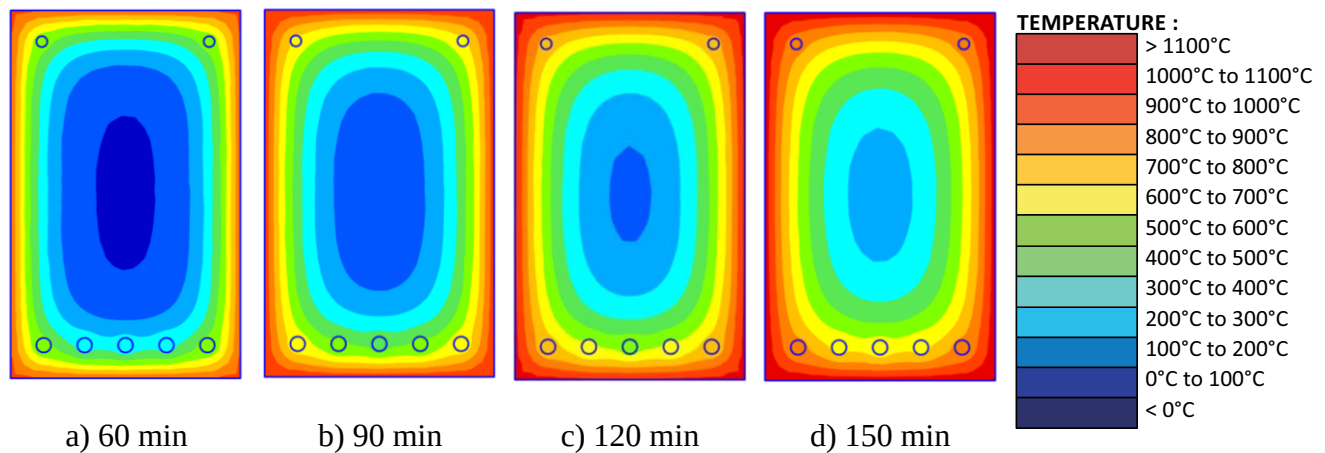


Fig. (13a-d). Distributions of temperature in cross-sections exposed to fire from four surfaces.

Fig. 13 contd....

3.2. Deflection-time Behavior

Figure 14 shows the deflection-time behavior of GFRP-steel RC beams with ρ_{ffs} of 0.2, 0.4, 0.6, and 0.8 exposed to fire, respectively. In these figures, the points for the deflection rate and deflection limit, as defined in BS EN1363-1:2020 [25], were also plotted. Equations 7 and 8 show the limits, where L (mm) is the beam span length and d (mm) is the effective height.

$$\text{Deflection limit: } D = \frac{L^2}{400d} \text{ (mm)} \quad (7)$$

$$\text{Deflection rate limit: } \frac{dD}{dt} = \frac{L^2}{9000d} \text{ (mm/min)} \quad (8)$$

Figure 14 plots the deflection-time curves of hybrid beams with the bottom surface exposed to fire. The round points present the deflection limit, and the square dots present the deflection rate limit. The fire times of these points are analyzed. As shown in this figure, the deflection-time curve is shifted downward and to the left, indicating that GFRP reinforcement of beams in fire is less advantageous than steel reinforcement. Another point observed from this figure is that the point corresponding to the deflection rate limit occurred prior to the point of deflection limit for beams with ρ_{ffs} of 0, 0.2, 0.4, and 0.6. However, when ρ_{ffs} increased to 0.8 and 1.0, the deflection limit points occurred after the deflection rate limit. This is attributed to the faster reduction in the mechanical properties of GFRP compared with that in steel. Therefore, the fire resistance of the hybrid GFRP-steel beams is considerably affected by ρ_{ffs} .

Figures 15-17 show the deflection-time curves of beams with 2, 3, and 4 surfaces of fire exposure, respectively. These curves also exhibited a phenomenon similar to that described above. In Fig. 15, the two points of deflection rate limit and deflection limit are close to each other for beams with ρ_{ffs} of 0.4 exposed to two surfaces. In Fig. (15), the deflection rate limit occurred prior to the deflection limit point. This result is due to the significant increase in temperature in the reinforcement, leading to a stronger reduction in its mechanical properties and, thus, the deflection rate limit occurring prior to the deflection limit.

An important point observed in Figs. (14-17) is that the fire resistance reduces significantly as the number of fire-exposed surfaces increases. This result is attributed to the fact that the cross-section temperatures were significantly affected by the number of fire-exposed surfaces.

3.3. The Effect of ρ_{ffs} on the Fire Resistance

Figure 18a-d, plot the fire resistance of hybrid beams with different conditions of fire exposure. The fire resistance decreased significantly when ρ_{ffs} increased from 0 to 1. Exposure to fire from the bottom surface, the fire resistance exhibited the strongest reduction with the increase in ρ_{ffs} (Fig. 18a). In contrast, the fire resistance exhibited the weakest reduction with the increase in ρ_{ffs} (Fig. 18d). The fire resistance of these hybrid GFRP-steel beams exposed to fire from the bottom surface is the highest, while that of beams exposed to fire from four surfaces is the lowest.

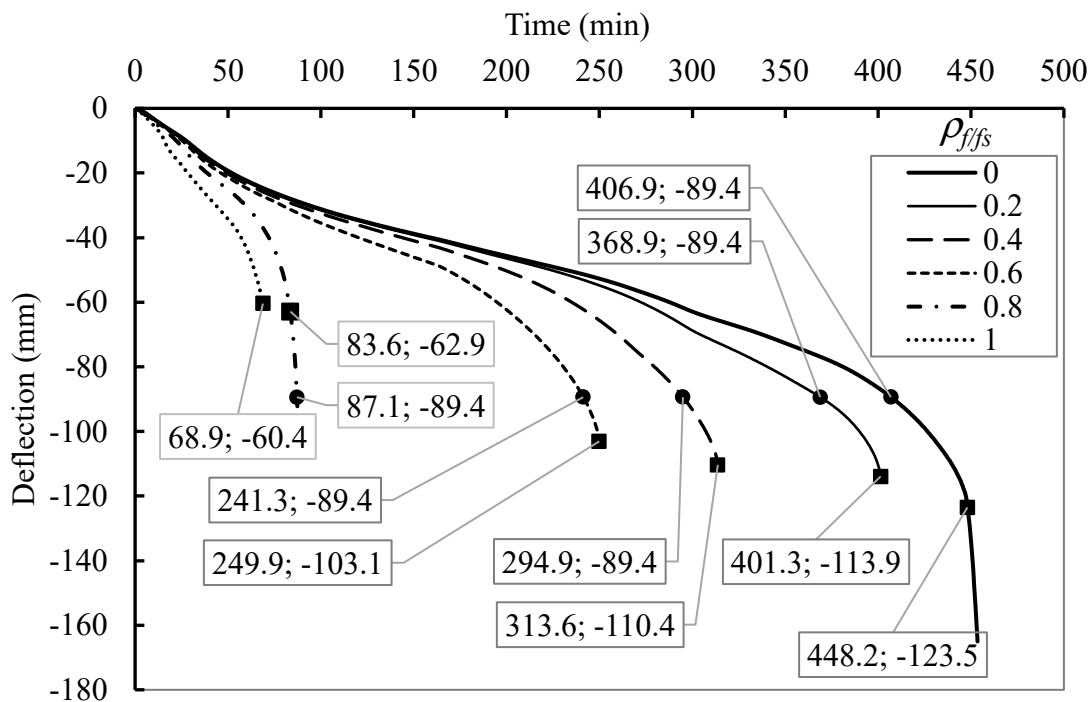


Fig. (14). Deflection-time behavior of beams with bottom surface exposed to fire.

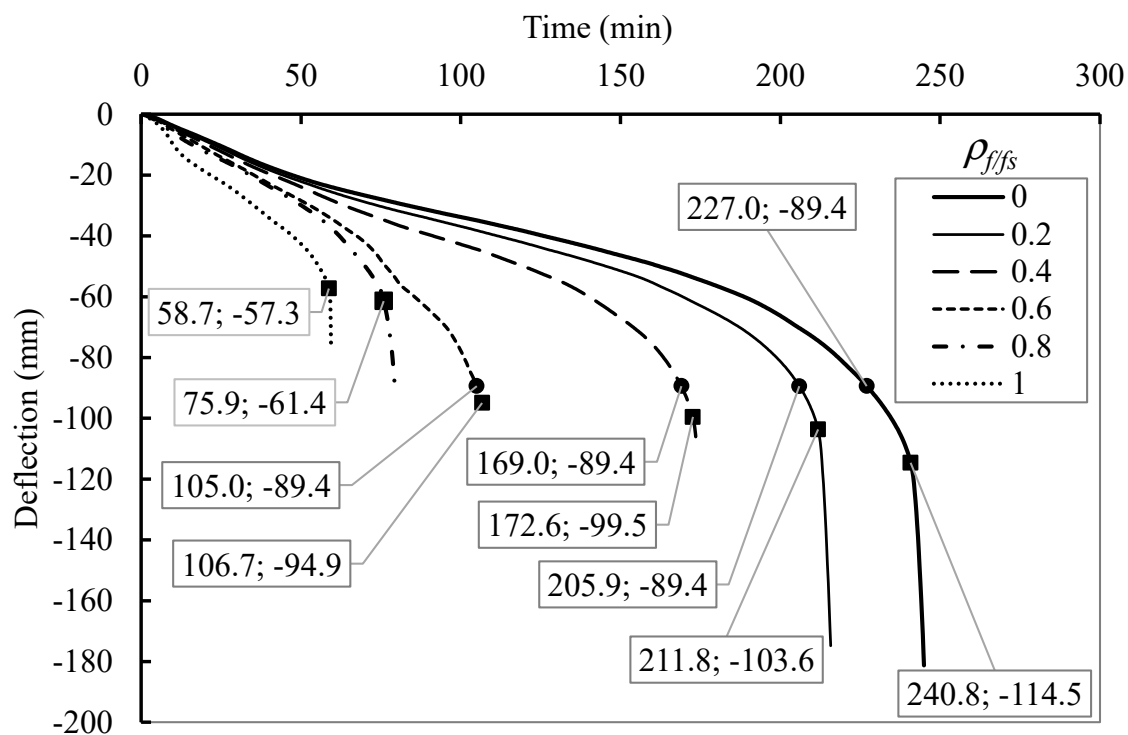


Fig. (15). Deflection-time behavior of beams with the bottom surface and one side surface exposed to fire.

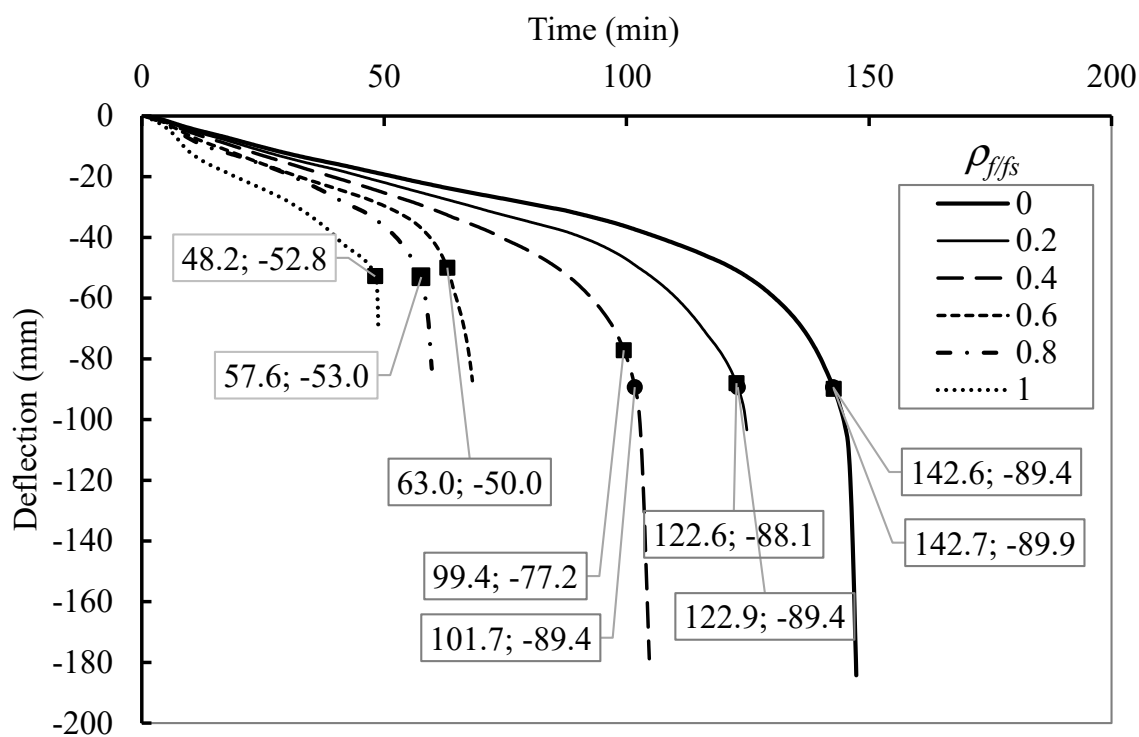


Fig. (16). Deflection-time behavior of beams with the bottom surface and two side surfaces exposed to fire.


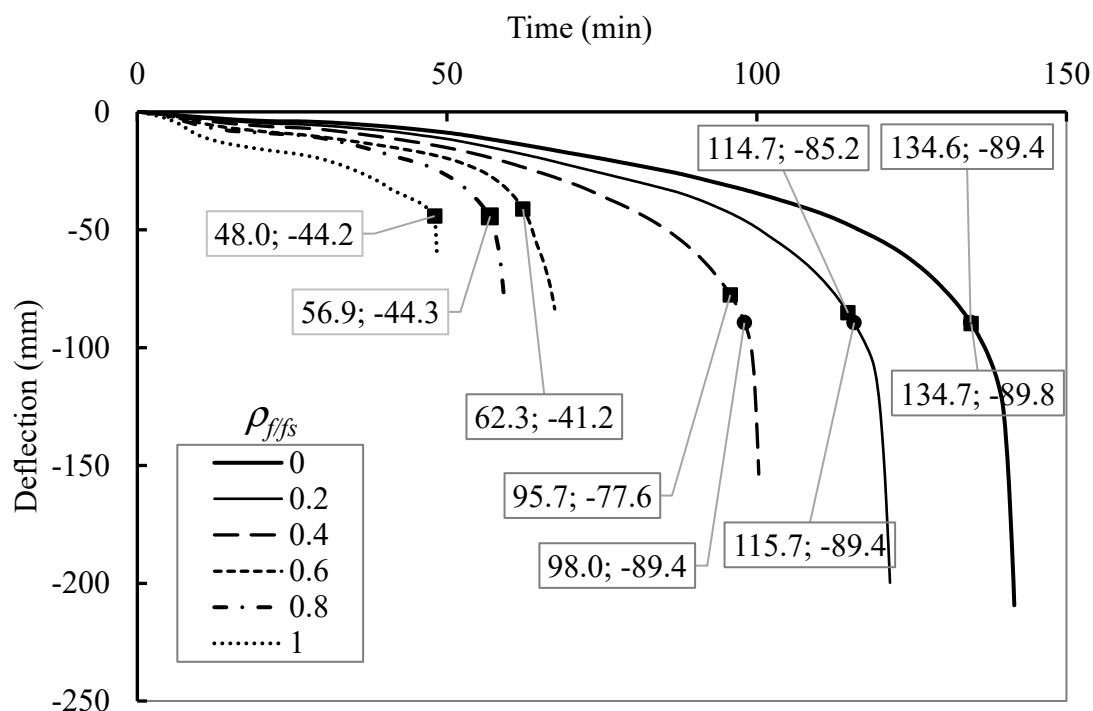



Fig. (17). Deflection-time behavior of beams with four surfaces exposed to fire.

Exposure to fire from the bottom surface (Fig. 18a), steel RC beams had a fire resistance of 406.9 minutes, which was reduced to 368.9, 294.9, 241.3, 83.6, and 68.9 minutes when the hybrid GFRP-steel RC beams had $\rho_{f/fs}$ of 0.2, 0.4, 0.6, and 0.8. When the concrete beam was reinforced with only GFRP $\rho_{f/fs} = 1$, the fire resistance was 68.9 minutes. Therefore, compared with the fire resistance


of the steel RC beam, the fire resistance of GFRP-steel RC beams with $\rho_{f/fs}$ of 0.2, 0.4, 0.6, and 0.8 was reduced by 9.3%, 27.5%, 40.7%, and 79.5%, respectively. When $\rho_{f/fs}$ increased to 1, the fire resistance was reduced by 83.1% compared with that of the steel RC beam. The fire resistance is significantly reduced with the increase in $\rho_{f/fs}$.

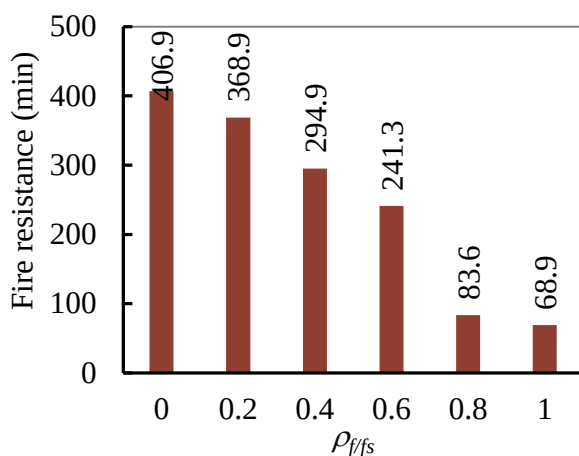


a) Beams with bottom surface exposed to fire

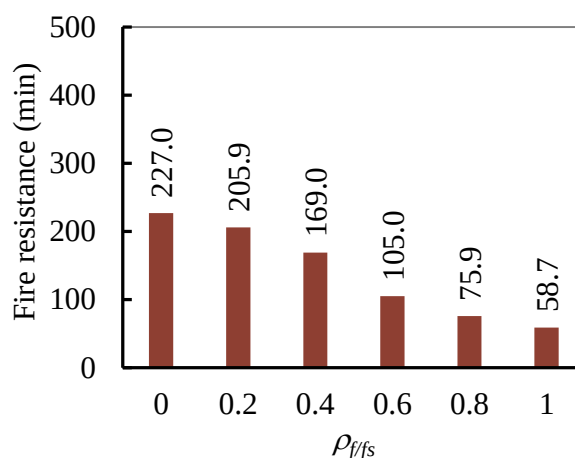

b) Beams with the bottom surface and one side surface exposed to fire

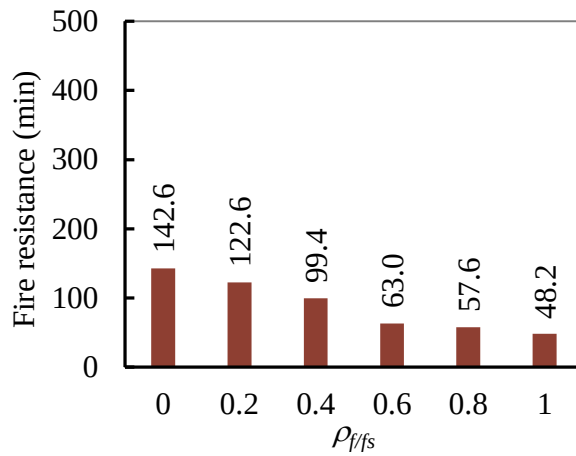

c) Beams with the bottom surface and two side surfaces exposed to fire

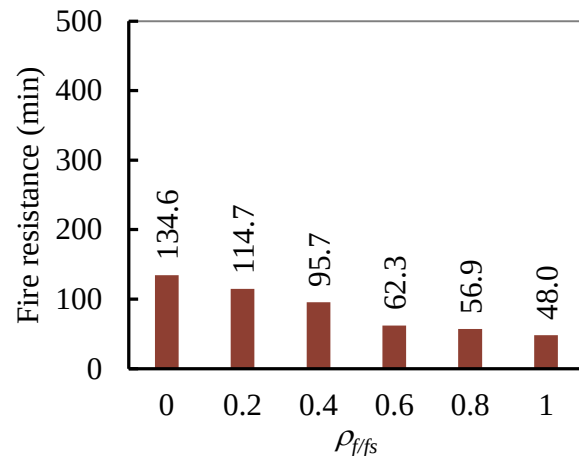


d) Beams with four surfaces exposed to fire

Fig. (18a-d). Fire resistance of hybrid GFRP-steel RC beams exposed to different fire conditions.


Exposure to fire from the bottom surface and one side surface (Fig. 18b), the fire resistance of the steel RC beam ($\rho_{f/fs}=0$) is 227 minutes. The fire resistance is reduced to 205.9, 169.0, 105.0, 75.9, and 58.7 minutes for beams with $\rho_{f/fs}$ of 0.2, 0.4, 0.6, 0.8, and 1.0, respectively. Compared with the fire resistance of the steel RC beam with $\rho_{f/fs}$ of 0, those of beams with $\rho_{f/fs}$ of 0.2, 0.4, 0.6, 0.8, and 1.0 were reduced by 9.3%, 25.6%, 53.7%, 66.6%, and 74.1%, respectively. Moving to the beams exposed to fire from three surfaces (Fig. 18c), these reduction percentages are 14%-62.2% when $\rho_{f/fs}$ varies from 0.2 to 1.0, respectively. Similarly, for beams exposed to four surfaces (Fig. 18d), the reduction percentages are 14.8%-64.3% when $\rho_{f/fs}$ varies from 0.2 to 1.0, respectively.

3.4. Effect of Number of Fire-exposed Surfaces on the Fire Resistance

The effect of the number of fire-exposed surfaces of beams with the same $\rho_{f/fs}$ on the fire resistance is examined as follows. Figure 19a-f show the fire resistance of hybrid beams with the same $\rho_{f/fs}$. These figures were plotted in the same axis limit coordinate system for visual comparisons. This figure indicates 1) the number of fire-exposed surfaces and 2) the importance of $\rho_{f/fs}$. Going from Fig. (19a) ($\rho_{f/fs} = 0$) to Fig. (19f) ($\rho_{f/fs} = 1$), the fire resistance reduces significantly. The effect of $\rho_{f/fs}$ on the fire resistance is presented previously. The following paragraph focuses on the variation in fire resistance with respect to the number of fire-exposed surfaces.

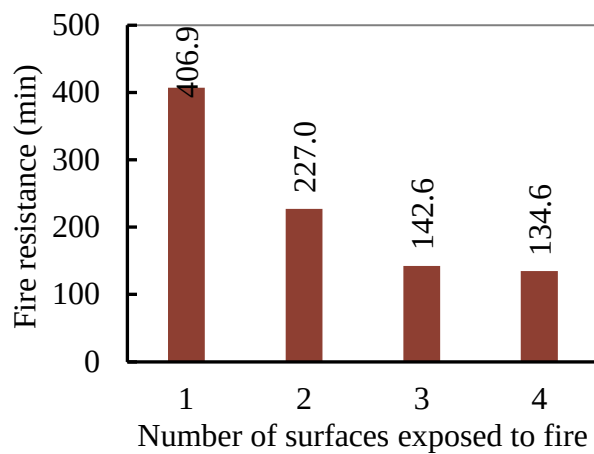

a) $\rho_{f/fs} = 0$

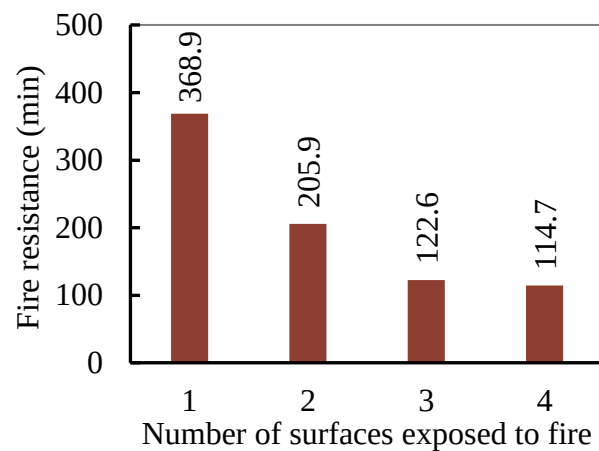

b) $\rho_{f/fs} = 0.2$

Fig. 19 contd.....

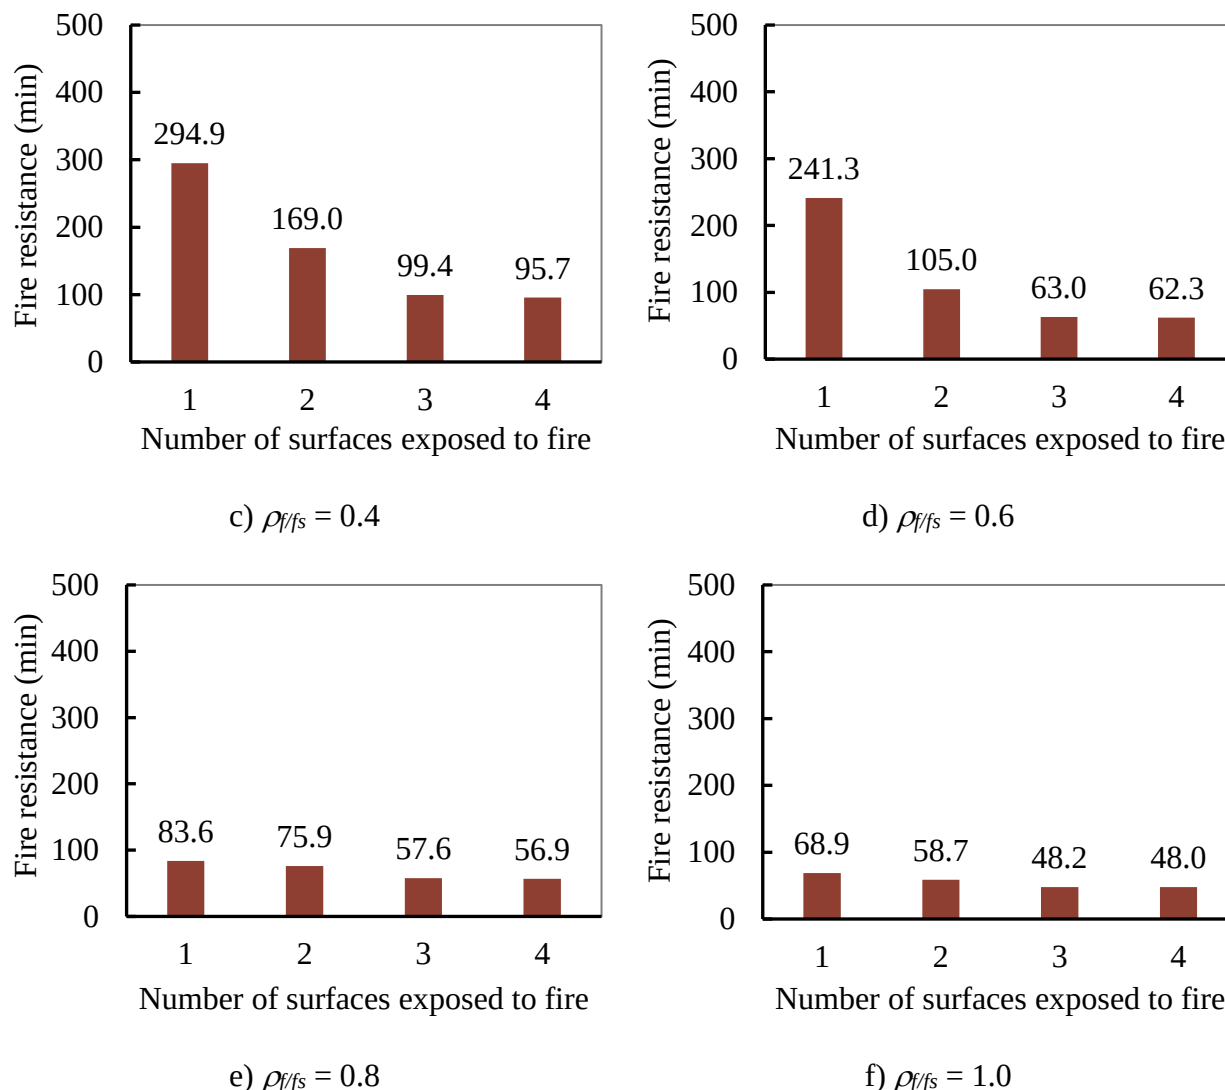


Fig. (19a-f). Effects of the number of fire-exposed surfaces on the fire resistance of hybrid GFRP-steel RC beams.

For beams with $\rho_{ffs} = 0$ (Fig. 19a), the fire resistance is 406.9 minutes when exposed to fire from the bottom surface. When the number of fire-exposed surfaces increases to 2, 3, and 4, the fire resistance reduces to 227.0, 142.6, and 134.6 minutes, respectively. The fire resistance of beams exposed to 2, 3, and 4 surfaces is reduced by 44.2%, 65.0%, and 66.9%, respectively, compared with that of beams exposed from the bottom surface. Beams with $\rho_{ffs} = 0.2$ (Fig. 19b) exposed to 1, 2, 3, and 4 surfaces had fire resistances of 368.9, 205.9, 122.6, and 114.7 minutes, respectively. Therefore, exposing 2, 3, and 4 surfaces reduces the fire resistance by 44.2%, 66.8%, and 68.9%, respectively, compared with

that of a beam exposed to fire from the bottom surface. With similar comparisons, the fire resistance of beams with $\rho_{ffs} = 0.4$ Fig. (19c) and 0.6 Fig. (19d) has reductions of 42.7-67.5% and 56.5-74.2%. However, when $\rho_{ffs} = 0.8$ Fig. (19e) and 1.0 Fig. (19f), the reductions in fire resistance are 9.2-31.9% and 14.8-30.3%, respectively. These reductions are presented in Fig. (20). When ρ_{ffs} increases from 0 to 0.6, the reduction percentage increases. Further increasing ρ_{ffs} results in a lower reduction percentage. These lower reduction values compared with the reductions in cases of low ρ_{ffs} are attributed to the dominance of GFRP bars.

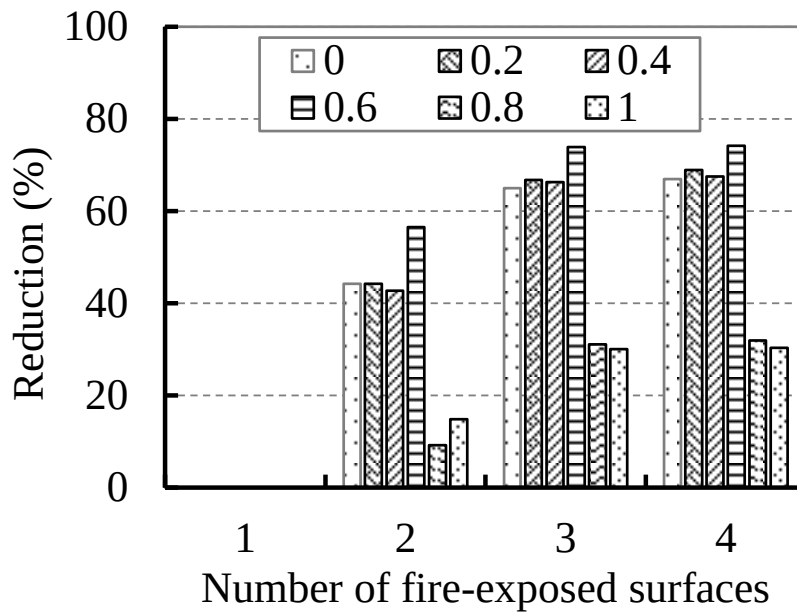


Fig. (20). Reduction in fire resistance compared with the fire resistance of beams exposed to the bottom surface.

4. STUDY LIMITATIONS AND FUTURE WORKS

Further studies should be encouraged for different beam geometries, cover thicknesses, load levels, support conditions, and thermal boundary conditions.

CONCLUSION

Based on the obtained results, conclusions are drawn as follows:

- Both the fire conditions and ρ_{ffs} detrimentally affected the deflection-time behavior and fire resistance of GFRP-steel RC beams. Combining the four fire-exposed surfaces and ρ_{ffs} of 1 resulted in the worst deflection-time behavior and the lowest fire resistance for the beams.
- When ρ_{ffs} increased from 0 to 1, the fire resistance of GFRP-steel RC beams was shifted from the state governed by the deflection limit to the state governed by the deflection rate limit. Increasing ρ_{ffs} from 0 to 1 reduced the fire resistance by up to 83.1%.
- Increasing the number of fire-exposed surfaces from 1 to 4 detrimentally affected the deflection-time behavior of the beams. Compared with exposure to the bottom surface, exposure to 2, 3, and 4 surfaces significantly decreased the fire resistance by up to 74.2%.

AUTHORS' CONTRIBUTIONS

The authors confirm their contributions to the paper as follows: D.V.D., V.V.C.: Study conception and design; D.V.D.: Analysis and interpretation of results; D.V.D., V.V.C.: Draft manuscript. All authors reviewed the results and approved the final version of the manuscript.

LIST OF ABBREVIATIONS

BFRP	= Basalt Fiber Reinforced Polymer
CFRP	= Carbon Fiber Reinforced Polymer
CONCEC	= Concrete material model according to Eurocode 1992-1-2 standards
FISO	= Function representing the ISO 834 Standard fire curve
FRP	= Fiber Reinforced Polymer
F20	= Constant ambient temperature function at 20°C in SAFIR
G	= Glass Fiber Reinforced Polymer bars
GFRP	= Glass Fiber Reinforced Polymer
NS CONCRETE	= Normal-Strength Concrete
RC	= Reinforced Concrete
S	= Steel bars
STEELEC2EN	= Steel material model according to Eurocode 1992-1-2 standards

CONSENT FOR PUBLICATION

Not applicable.

AVAILABILITY OF DATA AND MATERIALS

All data generated or analyzed during this study are included in this published article.

FUNDING

This research is funded by Vietnam National University Ho Chi Minh City, Vietnam (VNU-HCM) under grant number: B2024-20-08.

CONFLICT OF INTEREST

The authors declare no conflict of interest, financial or otherwise.

ACKNOWLEDGEMENTS

None.

REFERENCES

- [1] R. Djamaluddin, R. Irmawaty, Fakhruddin, and K. Yamaguchi, "Flexural behavior of repaired reinforced concrete beams due to corrosion of steel reinforcement using grouting and FRP sheet strengthening", *Civ. Eng. J.*, vol. 10, no. 1, pp. 222-233, 2024. [<http://dx.doi.org/10.28991/CEJ-2024-010-01-014>]
- [2] P. Selvachandran, S. Anandakumar, and K.L. Muthuramu, "Deflection behavior of prestressed concrete beam using fiber reinforced polymer (FRP) tendon", *Open Civ. Eng. J.*, vol. 10, no. 1, pp. 40-60, 2016. [<http://dx.doi.org/10.2174/1874149501610010040>]
- [3] Y.X. Liew, N. Bakar, K.S. Lim, S.I. Doh, R.P. Jaya, and S.C. Chin, "Shear strengthening of reinforced concrete beams using GFRP", *Open Civ. Eng. J.*, 2023. [<http://dx.doi.org/10.2174/18741495-v16-e221222-2022-53>]
- [4] A. El Refai, F. Abed, and A. Al-Rahmani, "Structural performance and serviceability of concrete beams reinforced with hybrid (GFRP and steel) bars", *Constr. Build. Mater.*, vol. 96, pp. 518-529, 2015. [<http://dx.doi.org/10.1016/j.conbuildmat.2015.08.063>]
- [5] L. Pang, W. Qu, P. Zhu, and J. Xu, "Design propositions for hybrid FRP-steel reinforced concrete beams", *J. Compos. Constr.*, vol. 20, no. 4, p. 04015086, 2016. [[http://dx.doi.org/10.1061/\(ASCE\)CC.1943-5614.0000654](http://dx.doi.org/10.1061/(ASCE)CC.1943-5614.0000654)]
- [6] R. Qin, A. Zhou, and D. Lau, "Effect of reinforcement ratio on the flexural performance of hybrid FRP reinforced concrete beams", *Compos., Part B Eng.*, vol. 108, pp. 200-209, 2017. [<http://dx.doi.org/10.1016/j.compositesb.2016.09.054>]
- [7] W. Qu, X. Zhang, and H. Huang, "Flexural behavior of concrete beams reinforced with hybrid (GFRP and Steel) bars", *J. Compos. Constr.*, vol. 13, no. 5, pp. 350-359, 2009. [[http://dx.doi.org/10.1061/\(ASCE\)CC.1943-5614.0000035](http://dx.doi.org/10.1061/(ASCE)CC.1943-5614.0000035)]
- [8] I.F. Kara, A.F. Ashour, and M.A. Koroğlu, "Flexural behavior of hybrid FRP/steel reinforced concrete beams", *Compos. Struct.*, vol. 129, pp. 111-121, 2015. [<http://dx.doi.org/10.1016/j.compstruct.2015.03.073>]
- [9] H. Abbas, A. Abadel, T. Almusallam, and Y. Al-Salloum, "Experimental and analytical study of flexural performance of concrete beams reinforced with hybrid of GFRP and steel rebars", *Eng. Fail. Anal.*, vol. 138, p. 106397, 2022. [<http://dx.doi.org/10.1016/j.engfailanal.2022.106397>]
- [10] A. Jebur Kadhim, and O. Hameed Zinkaah, "Load capacity prediction of hybrid (FRP/steel) reinforced concrete beams", *J. Struct. Integr. Maint.*, vol. 10, no. 2, p. 2496614, 2025. [<http://dx.doi.org/10.1080/24705314.2025.2496614>]
- [11] E. Alsuhailbani, and A. Aldukail, "Experimental study on hybrid steel-GFRP reinforced concrete beams with different stirrup types and spacings", *Buildings*, vol. 15, no. 22, p. 4047, 2024. [<http://dx.doi.org/10.3390/buildings15224047>]
- [12] A.J. Kadhim, and O.H. Zinkaah, "Numerical and theoretical investigation for the flexural behaviour of geopolymer concrete beams reinforced with hybrid FRP /steel bars", *J. Build. Eng.*, vol. 101, p. 111883, 2025. [<http://dx.doi.org/10.1016/j.job.2025.111883>]
- [13] J. He, J. Liu, N. Li, J. Li, and B. Fu, "Shear behavior of concrete beams reinforced with GFRP-steel hybrid stirrups", *Constr. Build. Mater.*, vol. 472, p. 140882, 2025. [<http://dx.doi.org/10.1016/j.conbuildmat.2025.140882>]
- [14] M.M. Rafi, and A. Nadjai, "Behavior of hybrid (steel-CFRP) and CFRP bar-reinforced concrete beams in fire", *J. Compos. Mater.*, vol. 45, no. 15, pp. 1573-1584, 2011. [<http://dx.doi.org/10.1177/0021998310385022>]
- [15] D.V. Doan, and V.V. Cao, "Fire behavior of concrete beams reinforced with various combinations of GFRP and steel", *Civil Engineering Journal*, vol. 11, no. 5, pp. 2045-2065, 2025. [<http://dx.doi.org/10.28991/CEJ-2025-011-05-018>]
- [16] H. Al-Thairy, "A simplified method for steady state and transient state thermal analysis of hybrid steel and FRP RC beams at fire", *Case Stud. Constr. Mater.*, vol. 13, p. e00465, 2020. [<http://dx.doi.org/10.1016/j.cscm.2020.e00465>]
- [17] N.H. Albu-Hassan, and H. Al-Thairy, "Experimental and numerical investigation on the behavior of hybrid concrete beams reinforced with GFRP bars after exposure to elevated temperature", *Structures*, vol. 28, pp. 537-551, 2020. [<http://dx.doi.org/10.1016/j.istruc.2020.08.079>]
- [18] A. Hassan, F. Khairallah, H. Elsayed, A. Salman, and H. Mamdouh, "Behaviour of concrete beams reinforced using basalt and steel bars under fire exposure", *Eng. Struct.*, vol. 238, p. 112251, 2021. [<http://dx.doi.org/10.1016/j.engstruct.2021.112251>]
- [19] M. Said, H. Hamdy, A.A. El-Sayed, and M.M. Khalil, "Structural efficiency of concrete beams reinforced with hybrid reinforcement bars under thermal loads", *J. Build. Eng.*, vol. 92, p. 109678, 2024. [<http://dx.doi.org/10.1016/j.job.2024.109678>]
- [20] CEN, EN 1992-1-1 (2004): Eurocode 2: Design of concrete structures - Part 1-1: General rules and rules for buildings, European Committee for Standardization, 2004.
- [21] T. Gernay, and J.M. Franssen, "A formulation of the Eurocode 2 concrete model at elevated temperature that includes an explicit term for transient creep", *Fire Saf. J.*, vol. 51, pp. 1-9, 2012. [<http://dx.doi.org/10.1016/j.firesaf.2012.02.001>]
- [22] M. Saafi, "Effect of fire on FRP reinforced concrete members", *Compos. Struct.*, vol. 58, no. 1, pp. 11-20, 2002. [[http://dx.doi.org/10.1016/S0263-8223\(02\)00045-4](http://dx.doi.org/10.1016/S0263-8223(02)00045-4)]
- [23] Y. Song, C. Fu, S. Liang, A. Yin, and L. Dang, "Fire resistance investigation of simple supported RC beams with varying reinforcement configurations", *Adv. Civ. Eng.*, vol. 2019, no. 1, p. 8625360, 2019. [<http://dx.doi.org/10.1155/2019/8625360>]
- [24] B. Yu, and V.K.R. Kodur, "Factors governing the fire response of concrete beams reinforced with FRP rebars", *Compos. Struct.*, vol. 100, pp. 257-269, 2013. [<http://dx.doi.org/10.1016/j.compstruct.2012.12.028>]
- [25] CEN, BS EN 1363-1:2020 Fire resistance tests - General requirements, BSI Standards Limited: Brussels, 2020.