

Elucidating the Pozzolanic Characteristics of Pastes Containing Circulating Fluidized Bed Fly Ash

Kae-Long Lin^{1,*}, Chao-Lung Hwang² and Yu-Min Chang³

¹Department of Environmental Engineering, National Ilan University, No. 1, Sec.1, Shen-Lung Rd., Yilan, 26047, Taiwan, ROC

²Department of Construction Engineering, National Taiwan University of Science and Technology, Keelung Rd., Sec. 4, Taipei 106, Taiwan, ROC

³Institute of Environmental Engineering and Management, National Taipei University of Technology, Taipei 106, Taiwan, ROC

Abstract: The aim of this study is to investigate the pozzolanic characteristics of circulating fluidized bed fly ash blended cement (CFBFABC) paste containing circulating fluidized bed fly ash (CFBFA). The initial and final setting time of CFBFABC pastes with CFBFA retards with an increasing CFBFA content. CFBFABC pastes containing 10% CFBFA exhibited a compressive strength similar to that of ordinary Portland cement pastes at the ages of 90 days. X-ray diffraction peaks indicated the presence of portlandite, ettringite, and unreacted C_3S (32.6°) and C_2S (41.9°). The gel/space ratio of the CFBFABC pastes increased with the curing time and decreased as the CFBFA content increased. The gel/space ratio increased with the curing time because of the progress of hydration, which led to some of the pores being filled. At the ages of 90 days, the gel/space ratio of the CFBFABC pastes containing 10% CFBFA increased to approximately 14%, it is possibly the consumption of $Ca(OH)_2$ and the formation of C-S-H in the CFBFABC pastes. The CFBFABC pastes containing 10% CFBFA did not exhibit any major decrease in the gel/space ratio. It exhibited favorable mechanical characteristics that were observed when the mixing ratio of CFBFA was 10%. Furthermore, CFBFA has the potential, as a pozzolanic material, partially to replace ordinary Portland cement.

Keywords: Circulating fluidized bed fly ash, compressive strength, gel/space ratio, hydration, Pozzolanic, setting time.

INTRODUCTION

Circulating fluidized bed combustion (CFBC) is an effective technology for high-sulfur coal burning, and SO_2 can be captured by adding limestone *in situ* during combustion [1, 2]. High-sulfur petroleum coke is a byproduct of the high-sulfur oil refining industry. Because of its high calorific value, it is often used as fuel along with coal in CFBC [3]. In a circulating fluidized bed (CFB) boiler, energy is generated by burning petroleum coke. To prevent the emission of a large amount of sulfur dioxide from blazed petroleum coke with a high sulfur content, limestone is introduced to the boiler for desulfurization. To increase the SO_2 removal efficiency, the CaO/SiO_2 ratio is often increased to 2.0-2.5. Moreover, there are many unreacted (CaO) and desulfurized ($CaSO_4$) products, and a small amount of $CaCO_3$ remains in the fly ash and bed ash of CFBC [1]. CFBC ash is produced at low combustion temperatures of 800-1000 °C; therefore, it may exhibit lower pozzolanic activity than does fly ash produced at higher temperatures [4].

In Taiwan, the petroleum industry produces approximately 800,000 tons of CFBC ash annually [5]. Recently,

energy saving and carbon reduction have been focuses worldwide, and thus, the concept of sustainable development has become popular. Emphasis on environmental protection has increased worldwide. Consequently, state-of-the-art research has focused on recycling and reusing industrial by-products. Currently, a wide range of construction-related industrial byproducts, including fly ash, silica fume, and water quenching slag, are used as cementing material to reduce cement consumption [6]. Pozzolans, when used as a partial cement replacement, are thought to improve the resistance of mortar or concrete to sulfate attack. The principal chemical effect of a pozzolan present in mortar is the removal of $Ca(OH)_2$ from the hydrating cement paste, leading to the formation of additional cement gel. In the case of a sulfate attack, upon exposure to a Na_2SO_4 solution, $Ca(OH)_2$ depletion in mortar is advantageous because $Ca(OH)_2$ provides Ca^{2+} ions for ettringite and gypsum formation, leading to the expansion and degradation of the mortar [7]. Previous investigations have indicated that CFB fly ash along with pressured fluidized bed combustion ash or pulverized fuel ash can be used to prepare cementless concrete [8-10]. Sheng's [11] investigation of the cementitious properties of fly ash produced by CFBC boilers cofiring coal and high-sulfur petroleum coke revealed that a high $f-CaO$ content and a high SO_3 content enhance cementitious properties; in other words, CFB fly ash is cementitious [12]. Freidin [13] indicated that a high total $f-CaO$ and $Ca(OH)_2$ content and high

*Address correspondence to this author at the Department of Environmental Engineering, National Ilan University, No. 1, Sec.1, Shen-Lung Rd., Yilan, 26047, Taiwan, ROC; Tel: +886-3-9357400ext 749; Fax: +886-3-9364277; E-mail: kllin@niu.edu.tw

SO₃ content contribute to a gradual increase in the compressive strength of fly ash and that curing significantly affects the strength of fly ash. Waste materials have traditionally been discarded in landfills and often dumped directly into ecosystems without adequate treatment. However, possible reuse or recycling alternatives should be investigated and implemented. The recent environmental approach aims to achieve sustainable development by conservation of natural resources and minimizing the discard of materials. Today, the reuse and recycling of waste materials after their potentialities have been detected is considered an activity that can contribute to diversify products, reduce production costs, provide alternative raw materials for a variety of industrial sectors, conserve non-renewable resources, save energy, and especially, improve public health [14]. Accordingly, this study evaluated the effect of CFB fly ash blended cement (CFBFABC) pastes on the pozzolanic reaction of CFB fly ash when the paste is adopted as a partial substitute for cement. Microstructural studies were conducted using X-ray diffraction (XRD) and gel/space ratios analyses.

MATERIALS AND METHODOLOGY

Materials

The CFBFA was obtained from a power plant in Taiwan. The CFBFA was homogenized; oven dried at 105°C for 24 hours; and then the chemical composition was characterized. American Society for Testing and Materials (ASTM) Type I Portland cement (OPC) from the Taiwan Cement Company was used in this study. It had a specific gravity was 3.15 and its physical-chemical properties met the requirements of ASTM C150. The major composition of the OPC is shown in Table 1.

Table 1. Chemical composition of CFB fly ash.

Chemical Composition (%)	CFB Fly Ash
SiO ₂	2.62
Al ₂ O ₃	0.99
Fe ₂ O ₃	0.52
CaO	51.95
MgO	1.26
SO ₃	25.74

Preparation of CFBFA

The CFBFA was then further pulverized in a ball mill until the particles could pass through a #200 mesh sieve. The CFBFA had a fineness value (on Blaine) of approximately 300 m²/Kg, with a specific gravity of 2.54. The resultant pulverized CFBFA was desiccated before being tested.

Preparation of CFBFA Blended Cement Paste Specimens

CFB fly ash blended cement (CFBFABC) pastes were produced by homogeneously mixing cement and water in a mixer. The levels of CFBFA substitution in the blended cement were between 10 and 40% by weight of the cement.

The water/binder (w/b) ratio of the CFBFABC paste was a constant of 0.4. CFBFABC paste cubes were prepared according to ASTM C109. The CFBFABC paste was poured into rectangular molds, which were kept under ambient conditions for 24 hours before being de-molded. After curing for 7, 14, 28, 56 and 90 days, the samples were subsequently crushed. Finally, the prepared samples were subjected to X-ray Diffraction (XRD) and gel/space ratios analyses.

Analysis Methodology

The major analyses performed on the CFBFABC pastes and its cube specimens included the following:

- (1) Setting time: The setting times of the cement mixes were determined according to ASTM C191 using a Vicat apparatus at room temperature. The initial setting time occurred when a Vicat needle 1 mm in diameter penetrated the sample to a point 5 ± 1 mm from the bottom of the mould. The final setting time was defined as when a 5-mm cap ring would leave no visible mark when placed on the surface of the sample.
- (2) Unconfined compressive strength (ASTM C39-72): At each testing age, four specimens were taken out of the moist room. The surfaces of the specimen were polished to make the two bearing surfaces flat and parallel. Three specimens were used for the compressive strength tests and one for the microstructural examination. The average strength value of the three specimens is presented. The coefficient of variation of these results was less than 10%.
- (3) Toxic characteristic leaching procedure (TCLP): SW 846-1311.
- (4) Leaching concentration: Cd (SW 846 -7131A), Pb (SW 846 -7421), Zn (SW 846-7951), Cu (SW846-7211), Cr (SW846-7191)
- (5) Mineralogy: The XRD analyses were carried out by a Siemens D-5000X-ray diffractometer with CuK α radiation and 2 θ scanning, ranging between 5° and 70°. The XRD scans were run at 0.05°-increments, with a 1 sec counting time.
- (6) Gel/space ratios and degree of hydration: The degree of hydration of the CFBFABC pastes was determined by thermal analysis. Thermogravimetric analysis instrument was employed to determine the hydration degree of the CFBFABC paste samples using the ignition method. The hydration degree of the CFBFABC pastes was then calculated as follows:

$$\alpha = \frac{(W_{105} - W_{580}) + 0.41(W_{580} - W_{1007})}{nW_{1007}} \times 100\% \quad (1)$$

$$X = \frac{0.68\alpha}{0.32\alpha + W/(C + P)}, \quad (2)$$

where

α : Hydration degree, %;

X: Gel/space ratio, %;

n: Evaporated water in the completely hydrated specimen; the n is equal to 0.24 for ordinary Portland cement paste;

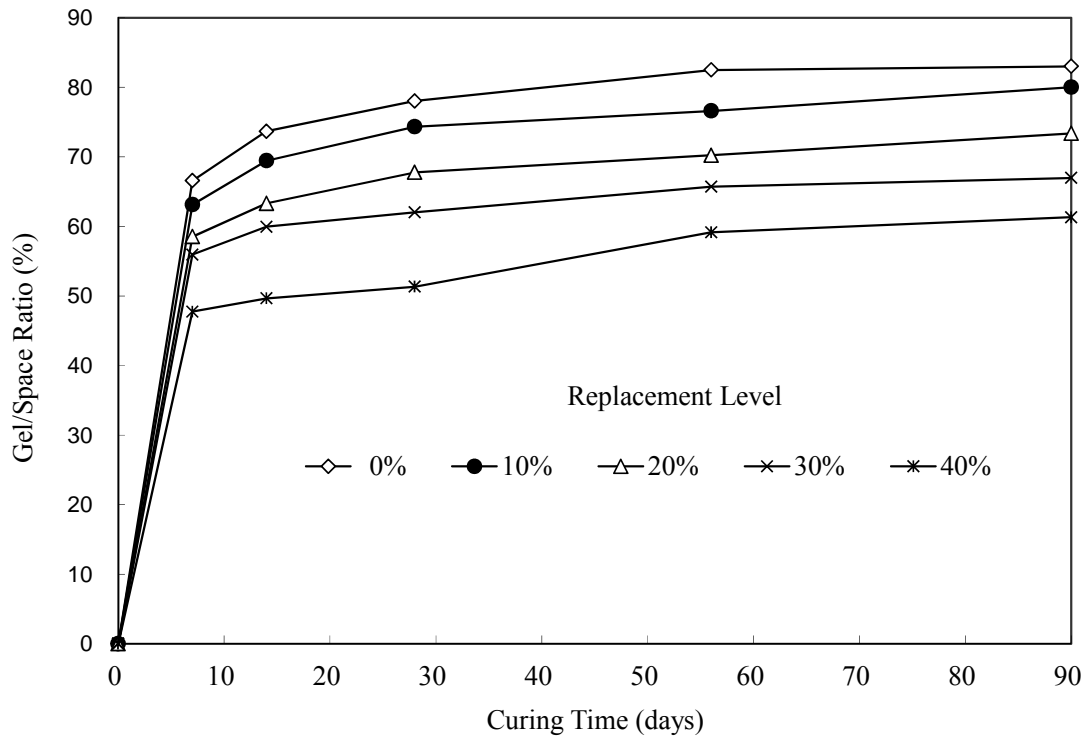


Fig. (6). Gel/space ratios of the CFBFABC pastes.

of a CFBFA-water system. Furthermore, the intensity of the XRD peaks of the unhydrated phases of C_2S and C_3S decreased when the curing time was increased because of the continuous hydration of these phases.

Gel/Space Ratios of CFBFABC Pastes

When the gel/space ratio is increased, the amount of hydration products increases; consequently, the synergistic effect of hydration products formed in the pores of the cement pastes enhances the compressive strength [12]. Fig. (6) shows the gel/space ratios of the CFBFABC pastes. The gel/space ratios increased with the curing time and decreased as the CFBFA content increased. The products of CFBFABC pastes, including hydrates of calcium silicate (CSH), ettringite, and Afm, were also expected to form with the consequent consumption of $Ca(OH)_2$. The gel/space ratios increased with the curing time, which led to part of the pores being filled. In addition, the gel/space ratios of the CFBFABC pastes decreased to a greater extent than did those of the OPC pastes. The volume change in SiO_2 in a pozzolanic reaction is caused by the production of CSH, it is possibly the low density of the hydration products and potentially leading to the filling of the pores. The production of a denser, close-textured structure of CFBFABC pastes containing 10% CFBFA increased the rate at which cement particles were hydrated. This increase led to a more densified and more homogeneous system and a considerable increase in the long-term strength. CFBFABC pastes containing 10% CFBFA did not exhibit large decreases in the gel/space ratio. The CFBFABC pastes containing 10% CFBFA did not exhibit any major decrease in the gel/space ratio. Furthermore, CFBFA has the potential, as a pozzolanic material, partially to replace ordinary Portland cement.

CONCLUSION

The results of this study can be summarized as follows. The initial and final setting time of CFBFABC pastes with CFBFA retards with an increasing CFBFA content. At the ages of 90 days, CFBFABC pastes containing 10% CFBFA exhibited a compressive strength similar to that of OPC pastes. X-ray diffraction peaks indicated the presence of portlandite, ettringite, and unreacted C_3S (32.6°) and C_2S (41.9°). The gel/space ratio of the CFBFABC pastes increased with the curing time and decreased as the CFBFA content increased. The gel/space ratio increased with the curing time because of the progress of hydration, which led to some of the pores being filled. At the ages of 90 days, the gel/space ratio of the CFBFABC pastes containing 10% CFBFA increased to approximately 14%, perhaps because of the initial attack of CFBFA, which played a major role in the formation of C-S-H and the consumption of $Ca(OH)_2$. It exhibited favorable mechanical characteristics were observed when the mixing ratio of CFBFA was 10%. Furthermore, CFBFA has the potential, as a pozzolanic material, partially to replace ordinary Portland cement.

CONFLICT OF INTEREST

The authors confirm that this article content has no conflict of interest.

ACKNOWLEDGEMENTS

Declared none.

REFERENCES

- [1] E. J. Anthony, and D. L. Granatstein, "Sulfation phenomena in fluidized bed combustion systems," *Prog. Energy Combust. Sci.*, vol. 27, no. 2, pp. 215-236, 2001.

- [2] E. J. Anthony, "Fluidized bed combustion of alternative solid fuels, status, successes and problems of the technology," *Prog. Energy Combust. Sci.*, vol. 21, no. 3, pp. 239-268, 1995.
- [3] G. H. Sheng, Q. Li, J. P. Zhai, and F. H. Li, "Self-cementitious properties of fly ashes from CFBC boilers co-firing coal and high-sulphur petroleum coke," *Cement Concr. Res.*, vol. 37, pp. 871-876, 2007.
- [4] J. Iribarne, A. Iribarne, J. Blondin, and E. J. Anthony, "Hydration of combustion ashes - a chemical and physical study," *Fuel*, vol. 80, pp. 773-784, 2001.
- [5] H. M. Hsu, A. Cheng, and S. J. Chao, "Reuse the bed ash from circulating fluidized bed combustion on mortar mixture," *J. Marine Sci. Technol.*, vol. 18, no. 4, pp. 620-628, 2010.
- [6] H. M. Hsu, "Effects of circulating fluidized bed combustion fly ash on the properties of alkali-activated slag cement mortars," *J. Marine Sci. Technol.*, vol. 20, no. 2, pp. 223-232, 2012.
- [7] M. O'Farrell, S. Wild, and B. B. Sabir, "Resistance to chemical attack of ground brick-PC mortar Part II. Synthetic seawater," *Cement Concr. Res.*, vol. 30, pp. 757-765, 2000.
- [8] C. S. Shon, A. K. Mukhopadhyay, D. Saylak, D. G. Zollinger, and G. G. Mejeoumov, "Potential use of stockpiled circulating fluidized bed combustion ashes in controlled low strength material (CLSM) mixture," *Construct. Build. Mater.*, vol. 24, pp. 839-847, 2010.
- [9] R. E. Conn, K. Sellakumar, and A. E. Bland, "Utilization of CFB Fly Ash for Construction Applications," In: *Proceedings of the 15th International Conference on Fluidized Bed Combustion*, 1999.
- [10] E. J. Anthony, E. E. Berry, J. Blondin, E. M. Bulewicz, and S. Burwell, "LIFAC ash - strategies for management", *Waste Manage.*, vol. 25, no. 3, pp. 265-679, 2005.
- [11] G. Sheng, Q. Li, J. Zhai, and F. Li, "Self-cementitious properties of fly ashes from CFBC boiler co-firing coal and high-sulphur petroleum coke," *Cement Concr. Res.*, vol. 37, pp. 871-876, 2007.
- [12] K. L. Lin, N. F. Wang, J. L. Shie, T. C. Lee, and C. Lee, "Elucidating the hydration properties of paste containing thin film transistor liquid crystal display waste glass," *J. Hazard. Mater.*, vol. 159, pp. 471-475, 2008.
- [13] Y. Shen, J. Qian, and Z. Zhang, "Investigations of anhydrite in CFBC fly ash as cement retarders," *Construct. Build. Mater.*, vol. 40, pp. 672-678, 2013.
- [14] R. R. Menezes, M. I. Brasileiro, L. N. L. Santana, G. A. Neves, H. L. Lira, and H. C. Ferreira, "Utilization of kaolin processing waste for the production of porous ceramic bodies," *Waste Manage. Res.*, vol. 26, pp. 362-368, 2008.
- [15] Y. Shen, J. Qian, and Z. Zhang, "Investigations of anhydrite in CFBC fly ash as cement retarders," *Construct. Build. Mater.*, vol. 40, pp. 672-678, 2013.
- [16] G. Sheng, J. Zhai, Q. Li, and F. Li, "Utilization of fly ash coming from a CFBC boiler cofiring coal and petroleum coke in Portland cement," *Fuel*, vol. 86, pp. 2625-2631, 2007.
- [17] T. Wu, M. Chi, and R. Huang, "Characteristics of CFBC fly ash and properties of cement-based composites with CFBC fly ash and coal-fired fly ash," *Construct. Build. Mater.*, vol. 66, pp. 172-180, 2014.

Received: September 08, 2014

Revised: January 13, 2015

Accepted: January 15, 2015

© Lin et al.; licensee Bentham Open.

This is an open access article licensed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/3.0/>) which permits unrestricted, non-commercial use, distribution and reproduction in any medium, provided the work is properly cited.